

Sound velocities and single-crystal elasticity of hydrous Fo90 olivine to 12 GPa

Luca Faccincani^{a,b,*}, Giacomo Criniti^c, Alexander Kurnosov^c, Tiziana Boffa Ballaran^c, Anthony C. Withers^c, Maurizio Mazzucchelli^d, Fabrizio Nestola^e, Massimo Coltorti^{a,b,f}

^a Department of Physics and Earth Sciences, University of Ferrara, Via Saragat 1, 44122 Ferrara, Italy

^b Department of Environmental and Prevention Sciences, University of Ferrara, C.so Ercole I D'Este 32, 44121 Ferrara, Italy

^c Bayerisches Geoinstitut, University of Bayreuth, Universitätsstraße 30, 95440 Bayreuth, Germany

^d Department of Chemical and Geological Sciences, University of Modena and Reggio Emilia, Via Campi 103, 41125 Modena, Italy

^e Department of Geosciences, University of Padua, Via Gradenigo 6, 35131 Padua, Italy

^f Istituto Nazionale di Geofisica e Vulcanologia (INGV) Sezione di Palermo, Via Ugo la Malfa 153, 90146 Palermo, Italy

ARTICLE INFO

Keywords:

Hydrous olivine
Brillouin scattering
Elasticity
High pressure
NAMs

ABSTRACT

Nominally anhydrous minerals (NAMs) may contain significant amounts of water and constitute an important reservoir for mantle hydrogen. The colloquial term ‘water’ in NAMs is related to the presence of hydroxyl-bearing (OH⁻) point defects in their crystal structure, where hydrogen is bonded to lattice oxygen and is charge-balanced by cation vacancies. This hydrous component may therefore have substantial effects on the thermoelastic parameters of NAMs, comparable to other major crystal-chemical substitutions (e.g., Fe, Al). Assessment of water concentrations in natural minerals from mantle xenoliths indicates that olivine commonly stores ~0–200 ppm of water. However, the lack of samples originating from depths exceeding ~250 km coupled with the rapid diffusion of hydrogen in olivine at magmatic temperatures makes the determination of the olivine water content in the upper mantle challenging. On the other hand, numerous experimental data show that, at pressures and temperatures corresponding to deep upper mantle conditions, the water storage capacity of olivine increases to 0.2–0.5 wt%. Therefore, determining the elastic properties of olivine samples with more realistic water contents for deep upper mantle conditions may help in interpreting both seismic velocity anomalies in potentially hydrous regions of Earth’s mantle as well as the observed seismic velocity and density contrasts across the 410-km discontinuity.

Here, we report simultaneous single-crystal X-ray diffraction and Brillouin scattering experiments at room temperature up to 11.96(2) GPa on hydrous [0.20(3) wt% H₂O] Fo90 olivine to assess its full elastic tensor, and complement these results with a careful re-analysis of all the available single-crystal elasticity data from the literature for anhydrous Fo90 olivine. While the bulk (*K*) and shear (*G*) moduli of hydrous Fo90 olivine are virtually identical to those of the corresponding anhydrous phase, their pressure derivatives *K'* and *G'* are slightly larger, although consistent within mutual uncertainties. We then defined linear relations between the water concentration in Fo90 olivine, the elastic moduli and their pressure derivatives, which were then used to compute the sound velocities of Fo90 olivine with higher degrees of hydration. Even for water concentrations as high as 0.5 wt%, the sound wave velocities of hydrous and anhydrous olivines were found to be identical within uncertainties at pressures corresponding to the base of the upper mantle. Contrary to previous claims, our data suggest that water in olivine is not seismically detectable, at least for contents consistent with deep upper mantle conditions. In addition to that, our data reveal that the hydration of olivine is unlikely to be a key factor in reconciling seismic velocity and density contrasts across the 410-km discontinuity with a pyroclitic mantle.

* Corresponding author at: Department of Environmental and Prevention Sciences, University of Ferrara, C.so Ercole I D'Este 32, 44121 Ferrara, Italy.

E-mail address: luca.faccincani@unife.it (L. Faccincani).

<https://doi.org/10.1016/j.pepi.2023.107011>

Received 22 October 2022; Received in revised form 23 February 2023; Accepted 13 March 2023

Available online 16 March 2023

0031-9201/© 2023 The Authors. Published by Elsevier B.V. This is an open access article under the CC BY license (<http://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Although commonly referred to as nominally anhydrous minerals (NAMs), the dominant phases of Earth's upper mantle may contain significant amounts of water (e.g., Bell and Rossman, 1992). The occurrence of water in NAMs is closely related to the presence of hydrogen in their crystal structures, which is bonded to oxygen atoms forming hydroxyl-bearing (OH^-) point defects, and its incorporation is typically charge-balanced by the formation of cation vacancies. Olivine, $\alpha\text{-(Mg,Fe)}_2\text{SiO}_4$, is considered to be the most abundant mineral of Earth's upper mantle and to constitute about 60 vol% of pyrolytic phase assemblages (Ringwood, 1975). The water concentration detected in natural olivine samples from mantle xenoliths is generally low, in the order of 0–200 ppm wt. (Beran and Libowitzky, 2006; Novella et al., 2015; Peslier et al., 2010). Although a growing body of water analyses of olivine is available in the literature (Bonadiman et al., 2009; Peslier, 2010; Xia et al., 2010, etc.), trends between water content and its distribution across different geological settings are still difficult to determine, as well as the actual abundance of water in olivine in the upper mantle. This is due to both the rapid diffusion of hydrogen in olivine at magmatic temperatures (e.g., Demouchy and Mackwell, 2006), which leads to partial dehydration of olivine in mantle xenoliths during their ascent, and the lack of xenoliths originating from depths greater than ~250 km. Even though the fast ascent of kimberlite magmas should prevent dehydration in olivine during xenolith transport (Demouchy et al., 2006; Peslier et al., 2008), in contrast to olivines from xenoliths found in alkali basalts which are commonly affected by H loss (e.g., Peslier et al., 2008), our understanding of how the water content of olivines changes as a function of depth largely relies on experimental studies. Indeed, a plethora of experimental data on water solubility in olivines at pressures and temperatures relevant to the upper mantle are available and indicate much higher water contents compared to those detected in natural olivine samples, especially at deep upper mantle conditions where the water storage capacity of olivine increases to 0.2–0.5 wt% (e.g., Férot and Bolfan-Casanova, 2012; Hirschmann et al., 2005; Mosenfelder, 2006). Therefore, synthetic olivine samples with a more realistic water content expected for deep upper mantle conditions warrant investigation, as this may improve our understanding of various geodynamic processes operating on Earth (Regenauer-Lieb, 2006).

Water incorporation in olivine, even in trace amounts, has long been known to have substantial effects on its physical and chemical properties, such as atomic diffusivity, electrical conductivity, thermal conductivity, rheology, and melting (e.g., Chang et al., 2017; Costa and Chakraborty, 2008; Inoue, 1994; Jung and Karato, 2001; Smyth et al., 2006). From a crystal-chemical perspective, hydrogen incorporation in the crystal structure of olivine may occur both in the octahedral M sites, $\text{Mg}^{2+} \leftrightarrow 2\text{H}^+$, and in tetrahedral T sites, $\text{Si}^{4+} \leftrightarrow 4\text{H}^+$ (e.g., Brodholt and Refson, 2000; Hushur et al., 2009; Smyth et al., 2006). Previous experimental studies about the substitution mechanism of water in olivine showed contrasting results, although it was recognized that the synthesis conditions (pressure and SiO_2 activity) were influencing factors (e.g., Bali et al., 2008; Férot and Bolfan-Casanova, 2012; Matveev et al., 2001; Withers and Hirschmann, 2008). However, recent electron microprobe (EPMA) data coupled with transmission Fourier transform infrared spectroscopy (FTIR) analyses (Fei and Katsura, 2020), solid-state nuclear magnetic resonance (NMR) spectroscopy (Xue et al., 2017), and first-principles calculations studies (Umamoto et al., 2011; Xue et al., 2017) suggest that hydrogen substitution in olivine mainly occurs at the T sites at high pressure. Therefore, hydrogen incorporation in the M sites can be ruled out from being the predominant substitution mechanism in olivine under typical mantle conditions, as its occurrence is restricted to shallow depths (≤ 80 km) and high SiO_2 activity (Bali et al., 2008; Fei and Katsura, 2020; Withers et al., 2011).

Despite its possible geophysical relevance, the effect of water on the elastic properties of olivine has been poorly constrained. The only elasticity measurements available in the literature were conducted by

Mao et al. (2010) on hydrous (0.89 wt% H_2O) end-member forsterite (Fo100) single crystals up to 14 GPa and by Jacobsen et al. (2008, 2009) on hydrous (0.8 wt% H_2O) Fo97 olivine single crystals at ambient pressure. These works showed that the incorporation of water into pure forsterite and near end-member compositions is accompanied by a considerable reduction of the adiabatic bulk (K_S) and shear (G) moduli at ambient conditions. However, owing to the much larger moduli pressure derivatives of the hydrated samples, K_S and G of the hydrous Fo100 at high pressure are greater than those of the corresponding anhydrous phase (Mao et al., 2010). Nonetheless, the effect of hydration on the elasticity of the more relevant Fo90 olivine mantle composition remains largely unconstrained because no experimental data are available. Furthermore, previous works studied hydrous samples containing 0.8–0.9 wt% H_2O , which is well above the expected water content for olivine at deep upper mantle conditions (e.g., Férot and Bolfan-Casanova, 2012; Hirschmann et al., 2005; Mosenfelder, 2006).

In this work, we set out to investigate the effect of hydration on the elastic properties of hydrous Fo90 olivine samples with more realistic water content for deep upper mantle conditions, as it may help in interpreting both seismic velocity anomalies in potentially hydrous regions of Earth's mantle as well as the observed seismic velocity and density contrasts across the 410-km discontinuity. To this aim, we performed simultaneous single-crystal X-ray diffraction (SCXRD) and Brillouin scattering measurements at room temperature up to 11.96(2) GPa on hydrous [0.20(3) wt% H_2O] Fo90 olivine to constrain its full elastic tensor. By comparing our new accurate data with those available from literature for anhydrous Fo90 olivine, we evaluated the combined effect of H_2O and Fe incorporation on the pressure-dependent elasticity of olivine. Our measurements are suitable to determine the sound wave velocities of hydrous Fo90 olivine at pressures corresponding to the base of the upper mantle, to be integrated in theoretical/experimental studies attempting to constrain the olivine abundance and water content at the 410-km discontinuity.

2. Materials and methods

Large (200–500 μm) and homogeneous single crystals of hydrous Fo90 olivine used in this study were previously synthesized and characterized by Withers et al. (2011, 2012, sample M475). Major element concentrations determined by wavelength-dispersive EPMA analysis indicate the Mg# of synthesized olivines to be 90.2(1), and water content was determined to be ~0.20(3) wt% based on elastic recoil detection analysis (ERDA) (Withers et al., 2012). Polarized FTIR spectroscopy and secondary ion mass spectroscopy (SIMS) measurements were also conducted on the same sample, showing excellent agreement with one another (Withers et al., 2012).

High-pressure Brillouin scattering measurements in DAC were conducted in the so-called platelet geometry (Speziale et al., 2014; Whitfield et al., 1976). For olivine, at least two crystal platelets with different crystallographic orientations are required to obtain the nine independent elastic stiffness coefficients (c_{ij}) given its orthorhombic symmetry. The full elastic tensor is obtained by a least-square fit of experimentally determined densities and sound wave velocities measured in different crystallographic directions using the Christoffel's equation:

$$|c_{ijkl}q_jq_l - \rho v_i^2 \delta_{ik}| = 0 \quad (1)$$

where c_{ijkl} are the elastic stiffness coefficients in tensorial notation (e.g., Nye, 1985), q_j and q_l are direction cosines, ρ is the density, v_i are the sound wave velocities and δ_{ik} is the Kronecker delta. To obtain accurate and precise c_{ij} values, it is important that their correlation in the fit procedure is low. This is achieved by using two appropriate crystallographic orientations (Criniti et al., 2021). We used published c_{ij} data for Fo90 olivine (Abramson et al., 1997) to simulate the shear (v_s) and compressional velocities (v_p) for different crystallographic planes. Synthetic v_s and v_p were randomly scattered by up to ± 30 or ± 60 m/s,

respectively, to simulate realistic datasets and to obtain realistic uncertainties in the inversion procedure. Platelets with direction cosines (0.32, 0.91, 0.26) and (0.78, 0.02, 0.62), corresponding to 101 and 161 *hkl* indices, were chosen for high-pressure measurements.

Hydrous Fo90 olivine single crystals were first observed under a polarising microscope and selected based on the absence of inclusions and their sharp optical extinction. Preliminary X-ray diffraction measurements were carried out on a Huber single-crystal diffractometer equipped with a point detector and MoK α radiation, and driven by the software SINGLE (Angel and Finger, 2011). Sharp diffraction peaks (full width half maxima $<0.055^\circ$) were observed upon omega-scan rotations for each crystal, confirming their high quality. Two crystals were selected and subsequently oriented parallel to the (101) or (161) crystallographic planes, glued on glass slides and polished on both sides to obtain platelets (crystals X1 and X2, respectively) with a thickness of $\sim 15\ \mu\text{m}$. The two platelets were then cut into semi-circular or rectangular shapes (Fig. 1) using a FEI Scios focused ion beam (Schulze et al., 2017), operated at 30 nA and 30 kV.

High-pressure SCXRD and Brillouin scattering measurements were carried out in a BX-90 piston-cylinder-type diamond anvil cell (DAC) (Kantor et al., 2012) equipped with Almax-Boehler diamond anvils having culets of 500 μm in diameter and conical seats with large opening angles (Boehler and De Hantsetters, 2004). A Re gasket was indented to a thickness of $\sim 70\ \mu\text{m}$ and drilled with an infrared laser to obtain the sample chamber. The two FIB-cut crystal platelets were loaded into the same sample chamber together with a ruby sphere (Fig. 1) for pressure determination following the calibration reported by Shen et al. (2020). Pre-compressed helium was loaded as quasi-hydrostatic pressure transmitting medium using the gas loading apparatus installed at the Bayerisches Geoinstitut, University of Bayreuth (Kurnosov et al., 2008).

High-pressure SCXRD and Brillouin scattering measurements were conducted using the system installed at the Bayerisches Geoinstitut, University of Bayreuth (Trots et al., 2011, 2013). The Brillouin scattering system consists of a Coherent Verdi V2 solid-state Nd:YVO $_4$ laser with a 532 nm single wavelength output and a six-pass Sandercock-type tandem Fabry-Perot interferometer (Sandercock, 1982) equipped with a

Hamamatsu C11202–50 detector. A source laser power of 100 or 150 mW was used for room pressure and high-pressure measurements, respectively. All measurements were performed in platelet geometry with an external scattering angle of 79.5° , which was calibrated using a fused silica glass standard. Periodic measurements of the standard revealed deviations within $\pm 0.1^\circ$, which correspond to shifts of up to $\pm 0.1\%$ in the calculated velocities, well within our experimental uncertainty. Dispersion curves of sound wave velocities versus crystallographic orientation were collected by rotation of the χ circle of the diffractometer between -170° and 180° at steps of 10° or 20° . Densities were derived at each pressure from single-crystal diffraction measurements, which were performed on the same goniometer using a Huber Eulerian single-crystal X-ray diffractometer equipped with a point detector. The system is coupled with an ultra-high intensity rotating anode X-ray source (MoK α , FR-E $^+$ SuperBright from Rigaku) operated at 55 kV and 45 mA and multilayer VaryMax $^{\text{TM}}$ focusing optics, and was driven by the software SINGLE (Angel and Finger, 2011). At each pressure point, 14–18 Bragg reflections for each crystal were centred using the eight position centring method (King and Finger, 1979), and cell parameters were determined by vector least-square refinement (Ralph and Finger, 1982).

3. Results and discussion

3.1. Compressibility of hydrous Fo90 olivine

High-pressure SCXRD measurements were conducted at seven pressure points, ranging from ambient pressure to $\sim 12\ \text{GPa}$. Unit-cell lattice parameters and volumes of both hydrous Fo90 olivine single crystals investigated in this study are reported in Table 1. The two crystals have slightly different volumes, $V(X1) > V(X2)$, with crystal X1 showing larger uncertainties on the measured lattice parameters. This is due to its crystallographic orientation, which limits the observations in both a^* and c^* . Therefore, lattice parameters measured for crystal X2 are likely more accurate. The variation with pressure of the lattice parameters and volumes, normalized with respect to their room pressure values, are

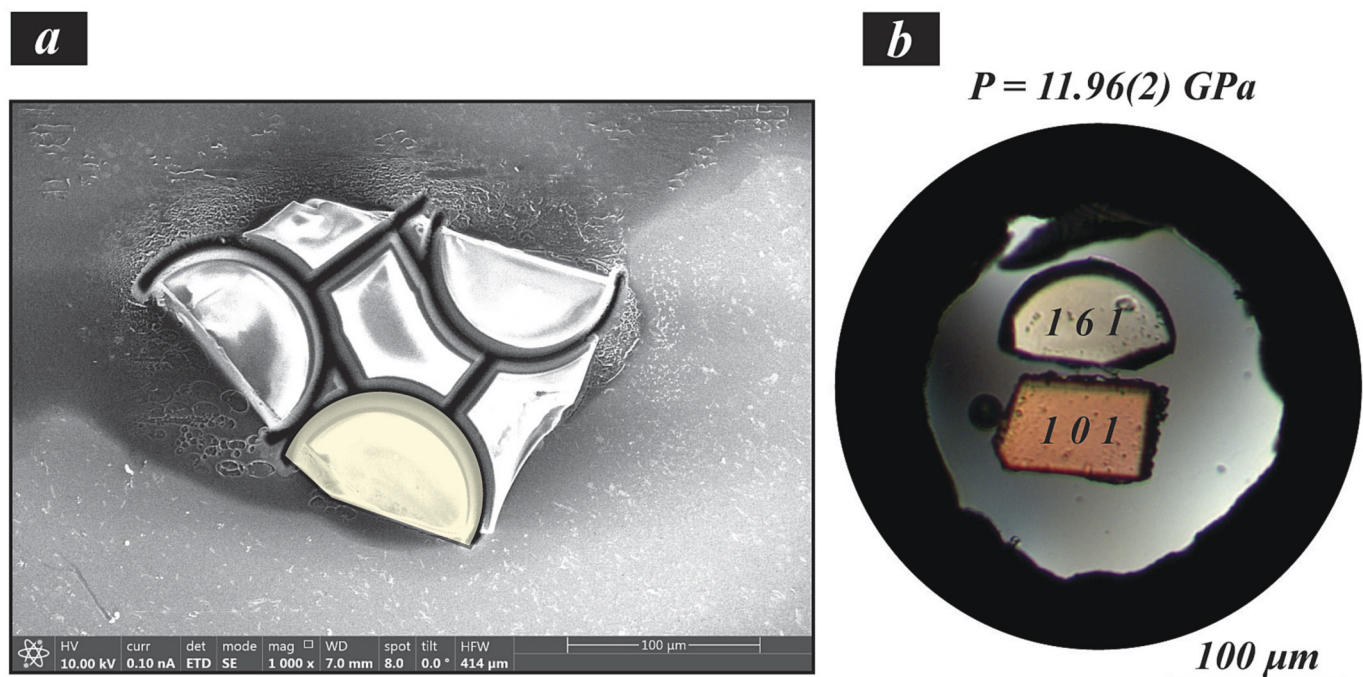


Fig. 1. (a) Secondary electron image of a Fo90 olivine platelet oriented parallel to the (161) plane (crystal X2) after the FIB cutting procedure; a superimposed yellow semicircle denotes the sample that was then loaded in the DAC. (b) Cross-polarized light photomicrographs of platelet X2 (161) and X1 (101) inside the sample chamber of the DAC at high pressure, together with a ruby chip (dark black sphere on the left of 101 platelet).

Table 1

Unit-cell lattice parameters and volumes of hydrous Fo90 olivine crystals X1 and X2 measured in the DAC experiment. Pressure is calculated using the ruby fluorescence calibration of Shen et al. (2020).

P (GPa)	X1 (platelet 1 0 1)				X2 (platelet 1 6 1)			
	a (Å)	b (Å)	c (Å)	V (Å ³)	a (Å)	b (Å)	c (Å)	V (Å ³)
0.00010(1)	4.7613(5)	10.2243(2)	5.9925(3)	291.72(3)	4.7610(1)	10.2227(3)	5.9921(1)	291.63(1)
1.40(2)	4.7499(7)	10.1753(3)	5.9701(5)	288.55(4)	4.7487(3)	10.1744(5)	5.9700(3)	288.44(2)
3.23(2)	4.7351(5)	10.1147(3)	5.9432(4)	284.64(3)	4.7342(2)	10.1128(4)	5.9423(2)	284.49(2)
5.53(4)	4.7178(7)	10.0455(3)	5.9116(5)	280.16(3)	4.7176(2)	10.0436(4)	5.9108(2)	280.06(2)
7.66(2)	4.7029(6)	9.9847(3)	5.8837(4)	276.28(3)	4.7028(3)	9.9824(7)	5.8826(3)	276.16(3)
9.60(4)	4.6902(7)	9.9313(3)	5.8592(6)	272.92(3)	4.6899(3)	9.9292(5)	5.8581(2)	272.80(2)
11.96(2)	4.6765(6)	9.8731(2)	5.8319(5)	269.27(3)	4.6762(2)	9.8707(4)	5.8309(1)	269.14(1)

reported in Fig. 2 and compared with literature data. Hydrous olivine is most compressible along the **b**-direction ([010]) and least compressible along the **a**-direction ([100]), as also observed for end-member Fo100 and Fo90 (e.g., Downs et al., 1996; Pamato et al., 2019). The EoSFit7c program was used to fit the *P*-*V* data of both crystals using a third-order Birch-Murnaghan Equation of State (BM3 EoS) (Angel et al., 2014):

$$P = \frac{3}{2}K_{T0} \left[\left(\frac{V_0}{V} \right)^{\frac{2}{3}} - \left(\frac{V_0}{V} \right)^{\frac{5}{3}} \right] \left\{ 1 + \frac{3}{4} (K'_{T0} - 4) \left[\left(\frac{V_0}{V} \right)^{\frac{2}{3}} - 1 \right] \right\} \quad (2)$$

where V_0 is the ambient pressure unit-cell volume, K_{T0} the isothermal bulk modulus and K'_{T0} its pressure derivative. The resulting BM-EoS parameters, simultaneously refined using the data weighted by the uncertainties in *P* and *V*, are: $V_0 = 291.65(2) \text{ Å}^3$, $K_{T0} = 124.5(1.0) \text{ GPa}$ and $K' = 4.5(2)$, where values in parenthesis correspond to 1σ uncertainties on each parameter. The fitted V_0 value is in excellent agreement (within 1σ) with the unit-cell volume measured at room pressure for crystal X2.

To judge the correctness of truncation of the BM-EoS to third order and to assess whether higher order terms (K'') might be significant in the EoS, we plotted the Eulerian finite strain (f_E) versus the normalized stress (F_E) (f_E - F_E plot; Angel, 2000) (Supplementary Fig. S1). Assessment of the f_E - F_E plot indicates that data are adequately described by a BM-EoS truncated to third order. Moreover, we have constructed confidence ellipses (Angel, 2000) in K_{T0} and K'_{T0} obtained for the fit to the hydrous olivine *P*-*V* dataset to visualise the extent of the correlation between such parameters and to assess the quality of the EoS (Supplementary Fig. S1). Following the approach of Angel (2000) and Angel et al. (2014), linearized BM3 EoSs have been used to fit the variation with pressure of the **a**-, **b**- and **c**-axis by substituting *V* with l^3 , $3K_{T0}$ with $M_{l,0}$ and $3K'_{T0}$ with $M'_{l,0}$:

$$P = \frac{1}{2}M_{l,0} \left[\left(\frac{l_0}{l} \right)^7 - \left(\frac{l_0}{l} \right)^5 \right] \left\{ 1 + \frac{1}{4} (M'_{l,0} - 12) \left[\left(\frac{l_0}{l} \right)^2 - 1 \right] \right\} \quad (3)$$

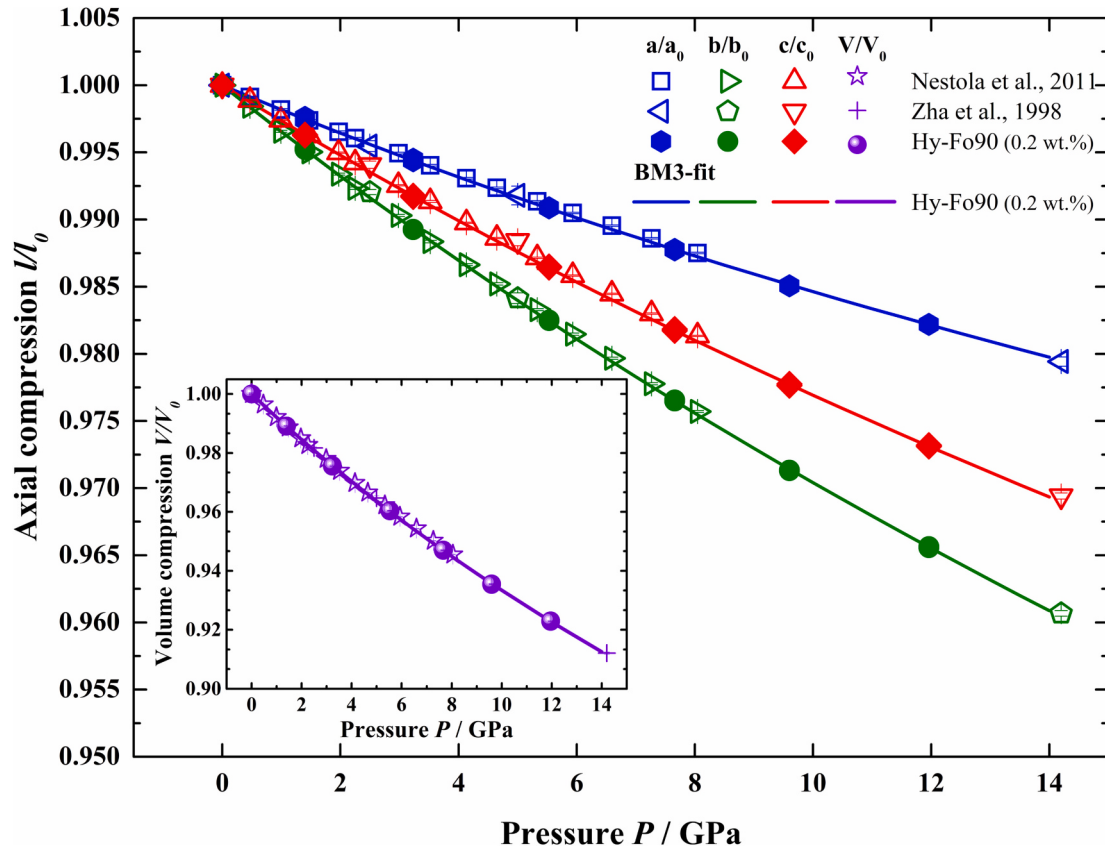


Fig. 2. Unit-cell parameters and unit-cell volumes (inset) of crystals X1 and X2 normalized to their room pressure values; data were fitted with a third-order Birch-Murnaghan EoS using the EoSFit7c program (Angel et al., 2014). Literature data of anhydrous Fo90–92 olivines (Nestola et al., 2011; Zha et al., 1998; Supplementary Table S1) are shown for reference. Note the good agreement between the BM3 fits and relative compression data of hydrous Fo90 olivine and the literature data for the corresponding anhydrous phase.

The resulting EoS parameters are: $a_0 = 4.7610(1) \text{ \AA}$, $M_{0a} = 539.1$ (5.7) GPa, $M'_a = 23.7(1.4)$, $b_0 = 10.2238(3) \text{ \AA}$, $M_{0b} = 283.4(2.8)$ GPa, $M'_b = 10.7(6)$ and $c_0 = 5.9921(1) \text{ \AA}$, $M_{0c} = 372.1(2.6)$ GPa, $M'_c = 12.1$ (5). As described in Angel et al. (2014), the linear moduli and their pressure derivatives defined in this fashion have numerical values three times those of the corresponding K_{T0} and, therefore, must be divided by three in order to return volume-like values. The resulting axial compressibility for the hydrous olivine follows the scheme $\beta_b > \beta_c > \beta_a$ (as observed for the anhydrous phase) and the obtained $M'_{l,0}$ and $M'_{l,0}$ values compare well with those of the anhydrous phase reported in the literature, as discussed later.

Angel et al. (2018) recently reviewed all the published single-crystal data that constrain the elastic properties and EoS of mantle-composition olivine (Fo90 to Fo92), also testing the mutual consistency of the different datasets used. Therefore, data selected by Angel et al. (2018) will be used as a comparison for hydrous olivine. The unit-cell lattice parameters reported by Nestola et al. (2011) and Zha et al. (1998), normalized to their corresponding room pressure values, are compared to the single crystal hydrous Fo90 olivine data obtained in this study (Fig. 2). When compared to the P - V and linearized BM3 EoS fits of the hydrous Fo90 olivine data obtained in this study, the relative compression curves (lattice parameters and volume) for the corresponding anhydrous phase show good agreement. Hence, we do not observe anomalies in the axial compressibility scheme or the unit-cell volume compression of the hydrous phase.

3.2. Sound wave velocities of hydrous Fo90 olivine and c_{ij} inversion strategy

Sound wave velocities of hydrous Fo90 olivine were measured at

seven pressure points, ranging from ambient pressure to ~ 12 GPa, i.e., the same conditions of SCXRD measurements (Table 2). Typical Brillouin spectra collected in the low- and high-pressure range (Fig. 3a) show distinct and resolved compressional (v_p) and shear (v_{s1} and v_{s2}) wave velocities peaks for most ranges of rotation angle (χ) of the diffractometer (Fig. 3b). To obtain the nine elastic stiffness coefficients c_{ij} , the Christoffel's equation (Eq. 1) is usually solved using a non-linear least-squares inversion of the density and all the acoustic velocities, collected with varying azimuthal angles, of the crystal platelets at each individual pressure point. This procedure has been referred to as individual fit in previous publications (Kurnosov et al., 2017; Criniti et al., 2021). Individual fits were performed at each pressure point by inverting all the measured acoustic velocities and density data, which were calculated self-consistently from the measured unit-cell volumes. Individual fits converged with small residuals at each pressure point (Fig. 3b) thanks to compressional and shear wave velocities being observed for most ranges of rotation angle (χ) and the low correlation between individual elastic stiffness coefficients resulting from the choice of the orientations of the two crystal platelets X1 and X2. Uncertainties in the determined c_{ij} values are generally $< 1\%$, except for c_{12} ($< 2\%$) (Table 2).

Recently, a non-conventional fitting procedure for Brillouin data (referred to as global fit) was proposed by Kurnosov et al. (2017) and described in detail in Buchen (2018). It consists of a global inversion of all sound velocity and density data, instead of independently inverting the data measured at each individual pressure point. This is practically done by fitting all sound velocity and density data with third-order finite strain EoSs describing the evolution with compression of each c_{ij} , using the formalism of Stixrude and Lithgow-Bertelloni (2005):

Table 2

Elastic stiffness coefficients (c_{ij}) and elastic moduli obtained from the individual fit and global fit procedure, reported in GPa. Numbers in brackets represent one standard deviation (std). ρ uncertainties propagate both the std.'s of the unit-cell volumes from SCXRD and the chemical composition from EPMA.

Individual Fits																
P (GPa)	ρ (g cm ⁻³)	c_{11}	c_{22}	c_{33}	c_{44}	c_{55}	c_{66}	c_{12}	c_{13}	c_{23}	K_{SV}	G_V	K_{SR}	G_R	K_{SVHR}	G_{VHR}
0.00010 (1)	3.345 (6)	319.2 (1.0)	195.7 (6)	232.7 (7)	63.2 (2)	77.1 (3)	77.8 (3)	71.7 (1.2)	69.6 (5)	73.5 (6)	130.8 (4)	79.2 (1)	126.5 (4)	76.2 (1)	128.7 (4)	77.7 (1)
1.40(2)	3.382 (6)	330.8 (6)	205.8 (4)	242.5 (5)	66.3 (2)	80.3 (2)	81.8 (3)	75.9 (1.1)	75.2 (6)	80.1 (4)	137.9 (4)	82.2 (1)	133.8 (4)	79.3 (1)	135.9 (4)	80.7 (1)
3.23(2)	3.428 (6)	342.8 (6)	215.6 (4)	254.0 (5)	69.8 (3)	82.7 (2)	85.3 (3)	83.4(9) (4)	83.4 (4)	87.1 (3)	146.7 (4)	84.8 (1)	142.4 (3)	82.0 (1)	144.5 (3)	83.4 (1)
5.53(4)	3.483 (6)	359.2 (1.1)	229.1 (4)	264.1 (6)	74.5 (2)	85.9 (5)	87.9 (5)	94.1 (1.8)	91.1 (7)	94.8 (6)	156.9 (5)	87.8 (2)	152.5 (5)	85.2 (1)	154.7 (5)	86.5 (1)
7.66(2)	3.532 (6)	374.3 (1.1)	238.6 (4)	276.2 (8)	77.4 (2)	88.7 (2)	93.3 (3)	101.9 (1.4)	98.7 (7)	102.3 (6)	166.1 (4)	91.0 (1)	161.3 (4)	88.2 (1)	163.7 (4)	89.6 (1)
9.60(4)	3.575 (6)	388.1 (1.2)	249.8 (6)	286.2 (9)	80.2 (2)	91.0 (3)	96.7 (3)	109.7 (1.8)	106.0 (7)	108.8 (8)	174.8 (5)	93.5 (1)	169.8 (5)	90.9 (1)	172.3 (4)	92.2 (1)
11.96(2)	3.624 (6)	404.0 (1.3)	260.7 (8)	296.5 (9)	83.6 (3)	94.0 (3)	99.8 (4)	115.6 (1.6)	116.1 (7)	118.2 (8)	184.6 (5)	96.2 (1)	179.4 (5)	93.5 (1)	182.0 (5)	94.8 (1)
Global Fit																
0.00010 (1)	3.345 (6)	319.2 (7)	197.4 (4)	233.9 (5)	63.8 (2)	77.6 (2)	78.5 (3)	72.4 (1.0)	69.9 (4)	74.3 (4)	131.5 (3)	79.6 (1)	127.4 (3)	76.6 (1)	129.5 (3)	78.1 (1)
1.440(7)	3.382 (6)	329.9 (7)	205.4 (4)	241.9 (5)	66.3 (2)	79.8 (2)	81.2 (3)	77.7 (1.0)	75.3 (4)	79.6 (4)	138.1 (3)	81.8 (1)	133.8 (3)	78.9 (1)	135.9 (3)	80.3 (1)
3.29(2)	3.428 (6)	343.2 (8)	215.5 (5)	252.0 (6)	69.6 (2)	82.4 (2)	84.7 (3)	84.5 (1.0)	82.3 (5)	86.3 (5)	146.3 (3)	84.5 (1)	142.0 (3)	81.7 (1)	144.2 (3)	83.1 (1)
5.62(3)	3.483 (6)	359.6 (9)	227.9 (5)	264.3 (7)	73.5 (2)	85.6 (2)	88.9 (3)	93.0 (1.2)	91.1 (5)	94.7 (6)	156.6 (4)	87.8 (1)	152.1 (4)	85.1 (1)	154.3 (4)	86.4 (1)
7.80(4)	3.532 (6)	374.5 (1.1)	239.3 (6)	275.6 (8)	77.1 (3)	88.6 (3)	92.8 (4)	101.0 (1.4)	99.2 (6)	102.5 (6)	166.1 (4)	90.8 (1)	161.4 (4)	88.1 (1)	163.7 (4)	89.5 (1)
9.80(5)	3.575 (6)	387.9 (1.2)	249.6 (7)	285.6 (9)	80.4 (3)	91.1 (3)	96.3 (4)	108.2 (1.6)	106.7 (7)	109.6 (7)	174.7 (5)	93.5 (1)	169.8 (5)	90.8 (1)	172.2 (5)	92.1 (1)
12.17(7)	3.624 (6)	403.4 (1.4)	261.5 (9)	297.3 (1.0)	84.2 (4)	94.1 (4)	100.3 (5)	116.7 (1.8)	115.5 (8)	118.0 (9)	184.7 (6)	96.5 (2)	179.7 (5)	93.8 (1)	182.2 (5)	95.2 (1)

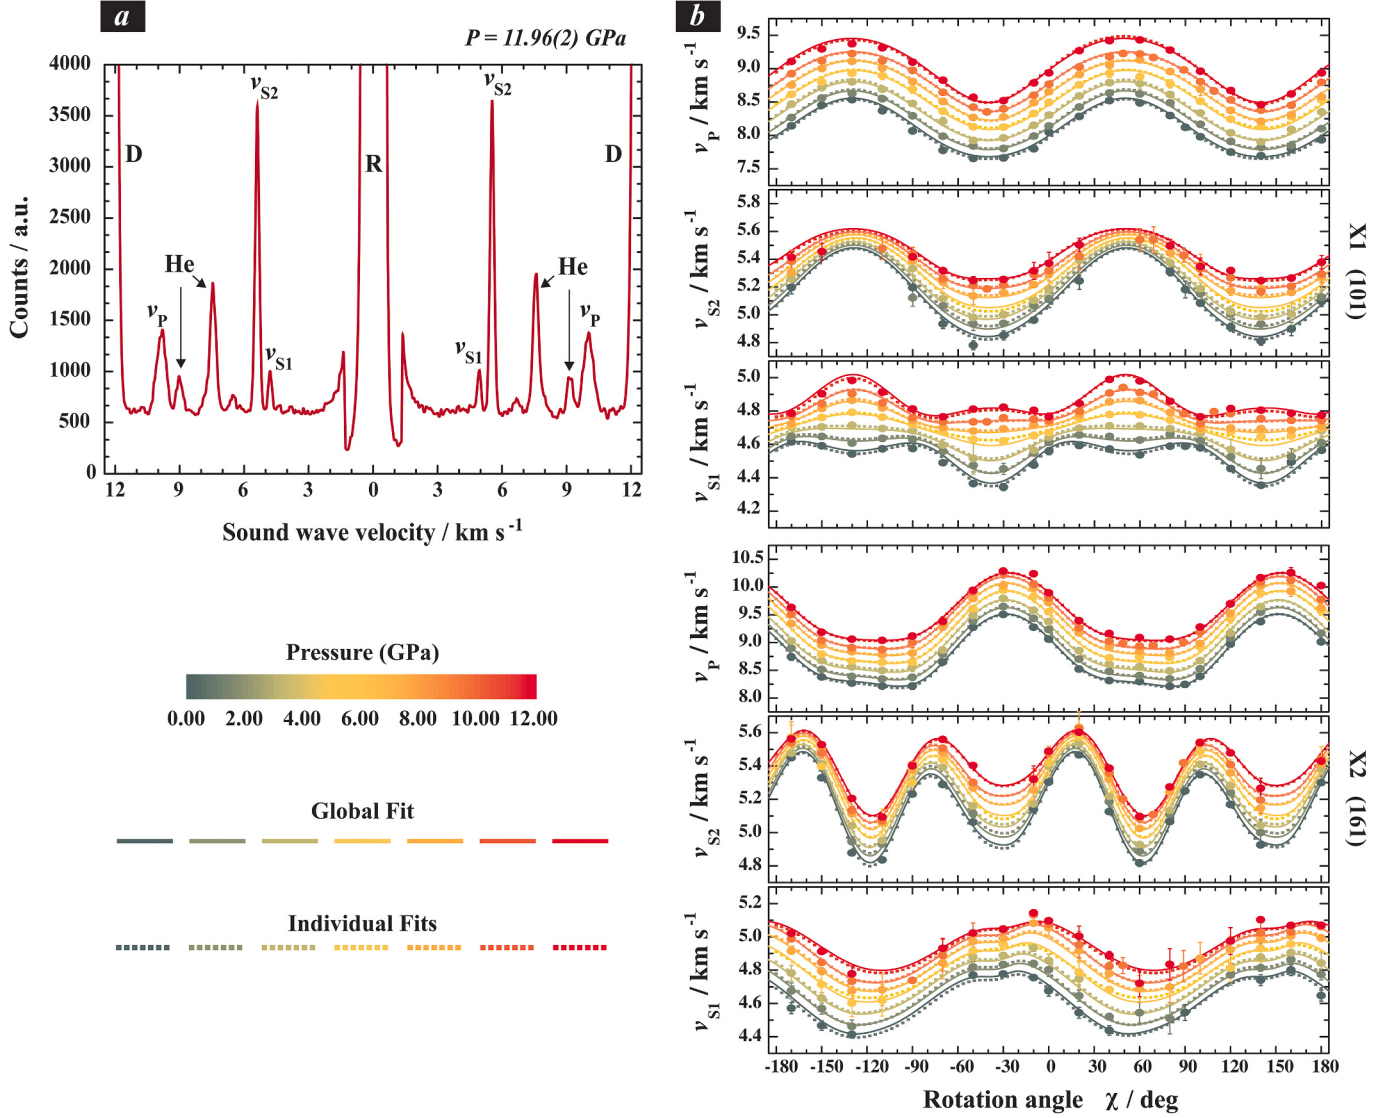


Fig. 3. (a) Selected Brillouin spectrum of crystal X2 (161) at 11.96(2) GPa showing distinct and well-resolved compressional v_P , slow and fast shear v_{S1} and v_{S2} wave velocities peaks, as well as spectral contributions of the diamond anvils (D), pressure medium (He) and elastic scattering (R). (b) Data points (filled symbols) as a function of the rotation angle (χ) for both platelets and dispersion curves obtained from the global fit (solid lines) and individual fits (dashed lines), showing excellent agreement between the two fitting strategies.

$$c_{ijkl} = (1 + 2f_E)^{\frac{5}{2}} \left\{ c_{ijkl,0} + (3K_0 c'_{ijkl,0} - 5c_{ijkl,0}) f_E + \left(6K_0 c'_{ijkl,0} - 14c_{ijkl,0} - \frac{3}{2} K_0 \delta_{kl}^{ij} (3K'_0 - 16) \right) f_E^2 \right\} \quad (4)$$

where c_{ijkl} is the elastic stiffness coefficient in tensorial notation at a given density (i.e., pressure), f_E is the finite Eulerian strain defined as $\frac{1}{2} \left[\left(\frac{\rho}{\rho_0} \right)^{\frac{2}{3}} - 1 \right]$, $c_{ijkl,0}$ is the elastic stiffness coefficient at ambient conditions and $c'_{ijkl,0}$ its pressure derivative, K_0 is the bulk modulus at ambient conditions and K'_0 its pressure derivative, and δ_{kl}^{ij} is equal to -3 for c_{1111} , c_{2222} , and c_{3333} and to -1 for the other six independent components of the elastic tensor. Thus, by refining the ambient-pressure stiffness coefficients ($c_{ij,0}$) and their pressure derivatives ($c'_{ij,0}$), a fit of all measured velocities at all pressure points is obtained. This approach has the advantage that all velocity data from all pressure points are used to constrain the c_{ij} s, minimizing the effect of data scattering on the calculated c_{ij} s and thus reducing their estimated uncertainties (Buchen,

2018). Even though this fitting procedure is particularly suited for very high pressure data, where some of the c_{ij} s are poorly constrained due to the lack of observations (e.g., Criniti et al., 2021), it can be applied to any high-pressure sound velocity dataset and the two procedures should yield consistent results as long as the collected data are of high quality, the high-pressure evolution of all c_{ij} is well described by a third-order finite strain EoS, and no phase transition takes place in the investigated pressure interval. Therefore, we also applied the global fit procedure to our dataset, which yielded very consistent results compared to those obtained by individual fits. The c_{ij} s calculated from two procedures show virtually no discrepancies, with values typically identical within two standard deviations (Table 2, Fig. 4).

Because density is measured at each pressure point, it is possible to

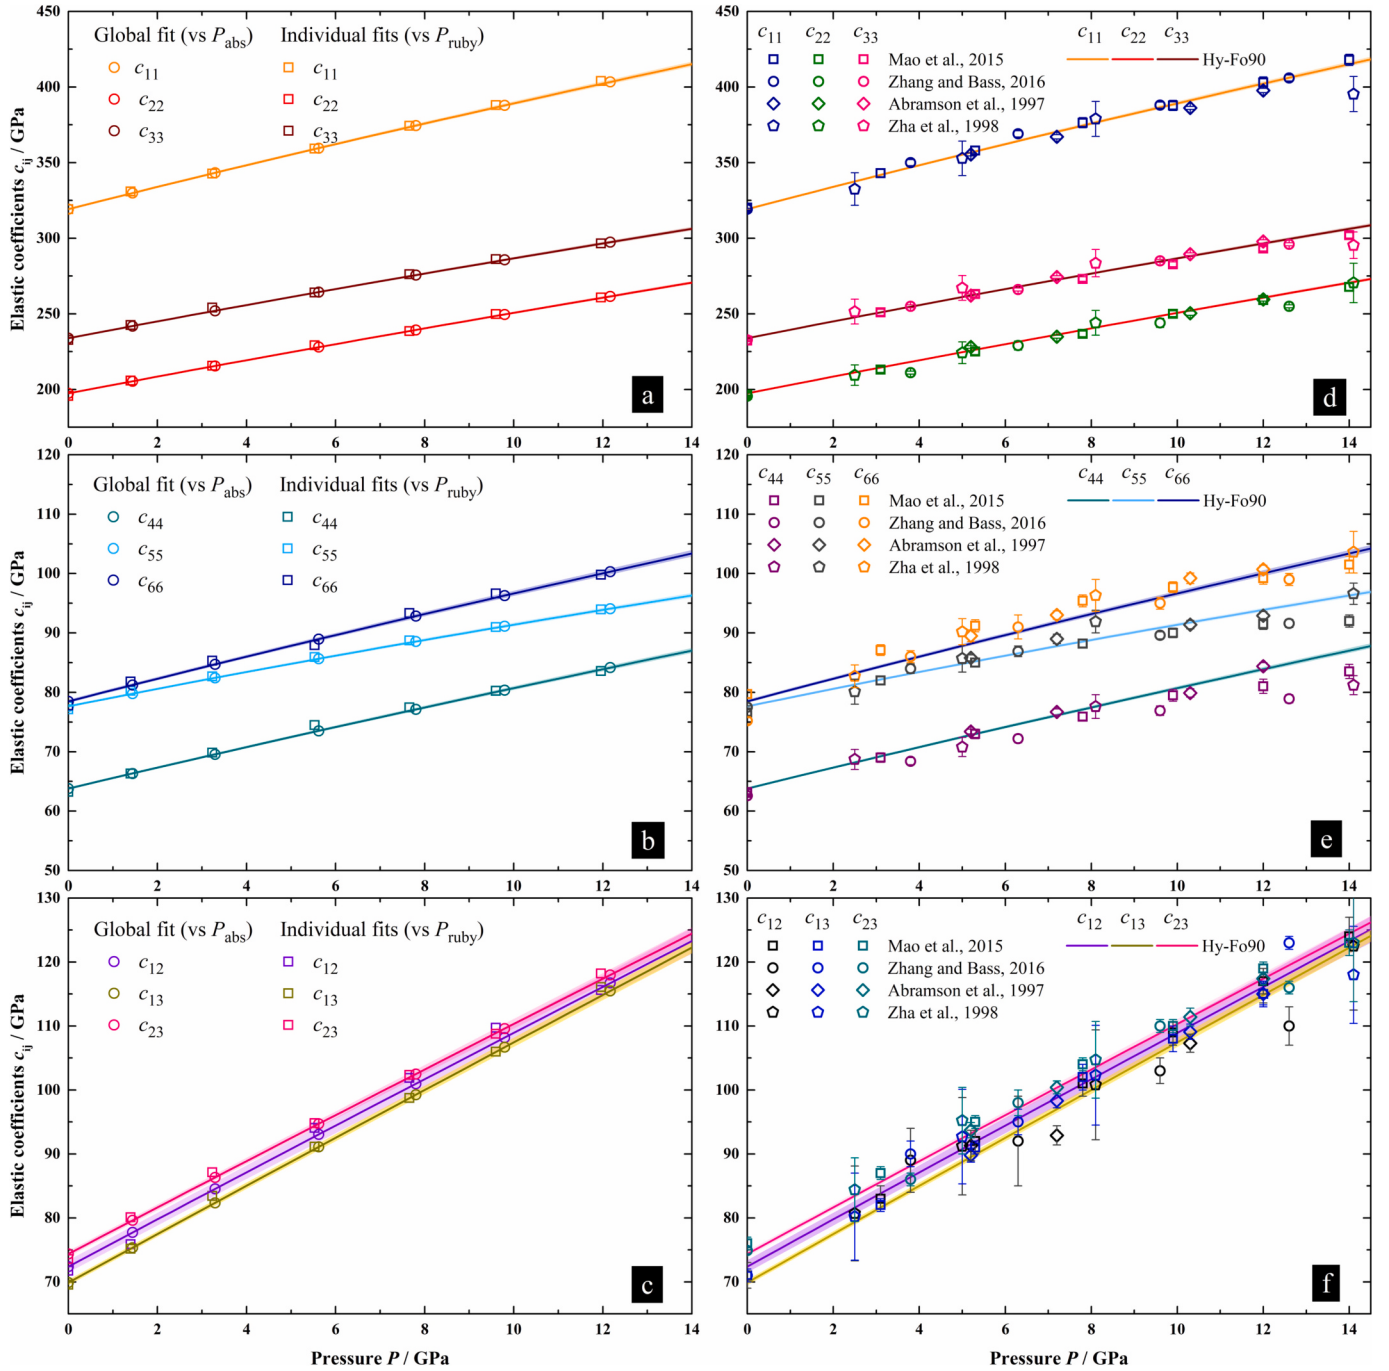


Fig. 4. (a-b-c) Comparison of the c_{ij} values obtained through the global fit (open circles) and individual fits (open squares), showing values typically identical within two standard deviations (Table 2); the solid lines represent third-order EoS fits of each c_{ij} (global fit parameters) (Table 3). (d-e-f) Comparison of the c_{ij} of anhydrous Fo90 olivines selected from previous literature (Abramson et al., 1997; Mao et al., 2015; Zha et al., 1998; Zhang and Bass, 2016; Supplementary Table S2), and the fit curves for each c_{ij} (global fit parameters) of hydrous Fo90 olivine obtained in this study. Note that the fits of the experimentally determined c_{ij} s for hydrous olivine and the c_{ij} s of the corresponding anhydrous phase are nearly identical.

calculate pressure without relying on a secondary scale (e.g., ruby) using the relative change in volume of the sample, obtained by X-ray diffraction, and the third-order finite strain equations described above. From these, an expression for the isothermal bulk modulus in the Reuss bound (K_{TR}) as a function of volume is obtained and the absolute pressure (P_{abs}) can be calculated by integrating K_{TR}/V over a given volume interval:

$$P_{abs} = \int_{V_0}^V \frac{K_{TR}(V)}{V} dV = 3K_{TR,0}f_E(1 + 2f_E)^{\frac{5}{2}} \left[1 + \frac{3}{2} \left(K'_{TR,0} - 4 \right) f_E \right] \quad (5)$$

where $K_{TR,0}$ is the bulk modulus at ambient conditions, $K'_{TR,0}$ is its pressure derivative, f_E is the finite Eulerian strain defined as $\frac{1}{2} \left[\left(\frac{V_0}{V} \right)^{\frac{2}{3}} - 1 \right]$. The experimentally determined adiabatic bulk modulus K_{SR} (Table 2) was converted into K_{TR} using the relations $K_{SR} = K_{TR}(1 + \alpha\gamma T)$ and $\alpha = \gamma C_V / K_{TR} V$. The thermoelastic parameters used for the conversion are $\theta_D = 644$ K, $\gamma_0 = 1.044$ and $q = 1.88$, corresponding to Fo90 (Angel et al., 2018), and are here assumed to be H_2O -independent. Then, $K_{TR,0}$ and $K'_{TR,0}$ were calculated by fitting a BM3 EoS to our K_T - V dataset. A comparison between the absolute pressure and the pressures

determined from the ruby fluorescence shift is plotted in Supplementary Fig. S2, along with the BM3 EoS fits to the $K_{SR}-\rho$ datasets obtained from the global and individual fits, which show excellent agreement.

Fig. 4 shows individual c_{ij} as a function of absolute pressure, as well as selected literature data for anhydrous Fo90 olivines for comparison, following the re-analysis of all the published single crystal data proposed

strain EoS to obtain the elastic moduli at ambient conditions (K_{S0} and G_0) and their pressure derivatives (K'_{S0} and G'_0) using the finite strain EoS of [Stixrude and Lithgow-Bertelloni \(2005\)](#):

$$K = (1 + 2f_E)^{\frac{5}{3}} \left[K_0 + (3K_0K'_0 - 5K_0)f_E + \frac{27}{2} (K_0K'_0 - 4K_0)f_E^2 \right] \quad (6)$$

$$G = (1 + 2f_E)^{\frac{5}{3}} \left[G_0 + (3K_0G'_0 - 5G_0)f_E + \left(6K_0G'_0 - 24K_0 - 14G_0 + \frac{9}{2}K_0K'_0 \right) f_E^2 \right] \quad (7)$$

by [Angel et al. \(2018\)](#) (Supplementary Table S2). The longitudinal coefficients (c_{11} , c_{22} and c_{33}), the off-diagonal coefficients (c_{12} , c_{13} and c_{33}) and the shear coefficients c_{44} and c_{66} follow a nearly linear increase with pressure, whereas the shear coefficient c_{55} exhibits a slightly downward trend towards higher pressures. The longitudinal coefficients c_{11} , c_{22} , c_{33} and the shear coefficients c_{44} , c_{55} , c_{66} follow similar trends with pressure compared to the anhydrous phase; only c_{66} is slightly offset to lower values in the range of 5 to 10 GPa (Fig. 4e). The off-diagonal coefficients c_{12} , c_{13} , c_{23} are characterized by very similar values along the whole pressure interval, with the stiffness scheme being $c_{23} > c_{12} > c_{13}$. Due to the small differences in the magnitude of the off-diagonal coefficients, their values are frequently the same within uncertainties, especially at high pressure. The off-diagonal coefficients c_{12} , c_{13} , c_{23} of the anhydrous phase are scattered but show comparable trends with those of the hydrous phase, especially c_{23} . Even if c_{13} is generally stiffer than c_{12} , in contrast with the hydrous phase, their systematics is more complex, as either they frequently cross over or are the same within uncertainties. Third-order finite strain EoSs (Eq. 4) were also used to fit the selected c_{ij} for anhydrous Fo90 olivines (Supplementary Table S2); the determined $c_{ij,0}$ and $c'_{ij,0}$ are reported in Table 3. The longitudinal, shear and off-diagonal coefficients of hydrous and anhydrous Fo90 olivines are identical within two standard deviations, and the same holds true for their pressure derivatives, except for $c'_{11,0}$ of hydrous Fo90 which is slightly larger. The fit curves of the c_{ij} s for hydrous and anhydrous olivine (Supplementary Fig. S3) are in good agreement with each other, except for c_{11} , c_{22} , c_{44} , and c_{55} of hydrous Fo90 which become moderately stiffer than their anhydrous corresponding at high pressure; this suggests a relatively small effect of water on the elastic properties of Fo90 olivine.

3.3. Elastic properties of hydrous Fo90 vs anhydrous Fo90 olivine

The adiabatic K_S and G were calculated from the c_{ij} values in the Reuss and Voigt bounds and in the Voigt-Reuss-Hill average at each experimental pressure point and are reported in Table 2. The elastic moduli obtained in this study were then fitted with third-order finite

Table 3

Resulting fit parameters of the third-order finite strain expression for the $c_{ij,0}$ and $c'_{ij,0}$ for hydrous Fo90 (as shown in Fig. 4) and anhydrous Fo90 (Supplementary Fig. S2).

	Hydrous Fo90 olivine		Anhydrous Fo90 olivine	
	$c_{ij,0}$	$c'_{ij,0}$	$c_{ij,0}$	$c'_{ij,0}$
c_{11}	319.2(7)	7.18(9)	320.0(9)	6.65(12)
c_{22}	197.4(4)	5.41(5)	195.9(9)	5.17(11)
c_{33}	233.9(5)	5.43(7)	233.2(6)	5.35(8)
c_{44}	63.8(2)	1.72(2)	63.2(4)	1.61(5)
c_{55}	77.6(2)	1.45(2)	77.7(3)	1.34(5)
c_{66}	78.5(3)	1.87(3)	78.0(6)	1.93(7)
c_{12}	72.4(1.0)	3.57(12)	71.3(1.1)	3.40(14)
c_{13}	69.9(4)	3.67(5)	71.0(7)	3.74(10)
c_{23}	74.3(4)	3.52(6)	75.4(7)	3.39(9)

The EoS parameters for K and G in the Voigt and Reuss bound are reported in Table 4. Both K_S and G show a monotonic increase with pressure (Fig. 5a) and are perfectly described by third-order EoS.

To quantify the effect of 0.20 wt% H₂O on the Fo90 elastic properties, the EoS parameters for hydrous Fo90 olivine determined in this study have to be compared to those of the corresponding anhydrous phase. The elastic behaviour of anhydrous Fo90 olivine has been largely investigated in the past decades and its full elastic tensor has been constrained by a variety of techniques. [Angel et al. \(2018\)](#) presented a re-analysis of all available single crystal data for mantle-composition olivine (Fo90–92) providing best-fit EoS parameters, which were recently used to calculate olivine density profiles over the upper mantle under different thermal regimes ([Faccincani et al., 2021](#)). However, a comparison of the EoS parameters determined in this study with those from [Angel et al. \(2018\)](#) cannot be made for two main reasons: (i) a best fit of the shear modulus data is missing, (ii) the fit includes high-temperature volume data and high-pressure, high-temperature (HP–HT) elasticity data, which are not available for hydrous Fo90 olivine. For this reason, we refitted the high-pressure elasticity data (K_S and G) for anhydrous Fo90 originally used in the fit from [Angel et al. \(2018\)](#) with the same formalism used for hydrous Fo90 olivine (Eqs. 6 and 7). The utilised data correspond to Fo90 olivines, and were selected up to ~14 GPa, i.e., the uppermost limit of olivine stability field. In our examination, we also made a re-analysis of the available shear modulus data to provide the best fit for G_0 and G'_0 of anhydrous Fo90 olivine. K_S and G were recalculated from the c_{ij} values reported at high pressure by [Abramson et al. \(1997\)](#) where the data are complete (i.e., four pressure points), the data of [Zha et al. \(1998\)](#) (i.e., four pressure points), the data of [Mao et al. \(2015\)](#) (i.e., seven pressure points) and the data of [Zhang and Bass \(2016\)](#) (i.e., five pressure points) (Fig. 5b, Supplementary Table S2). The EoS parameters for K_S and G in the Voigt and Reuss bound are reported in Table 4.

The EoS parameters for hydrous and anhydrous Fo90 olivine at ambient conditions are consistent within errors, especially K and G (Table 4). A comparison of the two obtained sets of EoS parameters indicates that the incorporation of 0.20 wt% H₂O into the olivine crystal structure causes only a minor reduction in K_{S0} and G_0 of ~0.2% and ~0.7%, respectively, and an increase in K'_{S0} and G'_0 of ~2.5% and ~5%, respectively. This suggests a negligible effect of water incorporation on K and G of Fo90 olivine and a moderate, positive effect on K' and G' . For this reason, the elastic behaviour of hydrous and anhydrous Fo90 olivine is indistinguishable within uncertainties up to ~14 GPa. This is consistent with a recent high-pressure single-crystal X-ray diffraction study conducted on a sample of Fo95 olivine with a low water content (~0.15 wt% H₂O) ([Xu et al., 2020](#)), where hydrogen substitution is predominantly associated with the T site. As the effect of water on the elastic moduli and their derivatives in our Fo90 and Fo100 ([Mao et al., 2010](#)) may also depend on different H substitution mechanisms in olivine, besides distinct water contents, comparisons among different data should be made carefully. The Fo100 single crystals studied by [Mao et al. \(2010\)](#) were synthesized by [Smyth et al. \(2006\)](#), run SZ0408A, to which

Table 4

EoS parameters for K and G in the Voigt and Reuss bound for hydrous and anhydrous Fo90 olivine and $\Delta_{H_2O}M$ ($[M]/\text{wt\% H}_2\text{O}$) values calculated for hydrous Fo90 olivine and hydrous Fo100 forsterite.

<i>Anhydrous Fo90 olivine – best fit</i>								
	K_{SV}		G_V		K_{SR}		G_R	
M_0 (GPa)	131.8(1.0)		80.2(5)		127.5(1.0)		77.2(5)	
M'_0	4.29(14)		1.42(5)		4.33(14)		1.48(6)	
<i>This study – Hydrous Fo90 olivine (global fit parameters)</i>								
	K_{SV}	Effect of H_2O (%)	G_V	Effect of H_2O (%)	K_{SR}	Effect of H_2O (%)	G_R	Effect of H_2O (%)
M_0 (GPa)	131.5(2)	−0.2	79.57(6)	−0.7	127.4(2)	−0.1	76.70(6)	−0.6
M'_0	4.40(3)	2.5	1.49(1)	5.2	4.44(3)	2.6	1.55(1)	4.9
<i>$\Delta_{H_2O}M([M]/\text{wt\% H}_2\text{O})^1$ – Hydrous Fo90 olivine</i>								
	K_{SV}		G_V		K_{SR}		G_R	
M_0 (GPa)	−1.5(5.1)		−3.2(2.6)		−0.5(5.1)		−2.5(2.5)	
M'_0	0.55(72)		0.35(26)		0.55(72)		0.35(31)	
<i>$\Delta_{H_2O}M([M]/\text{wt\% H}_2\text{O})^1$ – Hydrous Fo100 forsterite [data from Mao et al., 2010 and Zha et al., 1996]</i>								
	K_{SV}		G_V		K_{SR}		G_R	
M_0 (GPa)	−4.0(8)		−2.7(4)		−2.8(7)		−2.6(4)	
M'_0 ²	0.33(23)		0.39(13)		0.33(23)		0.39(13)	
<i>Hydrous Fo90 olivine – extrapolation to 0.5 wt% H_2O</i>								
	K_{SV}	Effect of H_2O (%)	G_V	Effect of H_2O (%)	K_{SR}	Effect of H_2O (%)	G_R	Effect of H_2O (%)
M_0 (GPa)	131.1(2)	−0.5	78.60(6)	−2.0	127.3(2)	−0.2	76.00(6)	−1.5
M'_0	4.56(3)	6.4	1.60(1)	13.0	4.61(3)	6.4	1.66(1)	12.4

¹ $\Delta_{H_2O}M$ values yield the change in K , G , K' , and G' for a reference water content of 1 wt%.

² We assumed that M'_0 in the Voigt-Reuss-Hill bound $\approx M'_0$ in the Voigt and Reuss bounds.

the reader is referred for synthesis conditions and FTIR spectrum. For this sample, it was suggested that hydration predominantly occurred through the octahedral substitution $\text{Mg}^{2+} \leftrightarrow 2\text{H}^+$. On the other hand, a tetrahedral substitution $\text{Si}^{4+} \leftrightarrow 4\text{H}^+$ has been suggested for our sample (Withers et al., 2011). Note, however, that the FTIR spectra of hydrous Fo100 (Smyth et al., 2006, Fig. 2) and hydrous Fo90 (Withers et al., 2011, Fig. 2) both show strong absorbance features in the identical high wavenumber region, hinting that the two samples should present the same substitution mechanism. Various pieces of evidence suggest that absorption features in the high wavenumber region (~ 3.450 – 3.600 cm^{-1}) are related to OH bonding to T sites (Fei and Katsura, 2020; Umemoto et al., 2011; Xue et al., 2017), therefore we may expect that both the Fo100 and Fo90 sample contain predominantly Si vacancies. The important observation, however, for the aim of this study is that both samples present the same type of defects and therefore we can compare the effect of hydration on their elastic properties directly, upon normalization with respect to H_2O concentration. The effect of water on the elastic parameters can be then expressed as:

$$\Delta_{H_2O}M \left(\frac{[M]}{\text{wt\% H}_2\text{O}} \right) = \frac{M_{\text{hydrous}} - M_{\text{dry}}}{X_{\text{H}_2\text{O}} (\text{wt\%})} \quad (8)$$

where M can be K_{S0} , G_0 (in GPa), K'_0 or G'_0 (non-dimensional) and $X_{\text{H}_2\text{O}}$ is the water content of the hydrous sample in wt%. $\Delta_{H_2O}M$ values defined in this fashion yield the change in elastic properties for a reference water content of 1 wt%; the obtained results for both Fo90 and Fo100 are reported in Table 4. $\Delta_{H_2O}M$ values are affected by large uncertainties, especially in the case of Fo90. This mostly arises from the fitting parameters of anhydrous Fo90, which are less well-constrained because four different datasets were combined in the EoS fit of the elastic moduli (Table 4). $\Delta_{H_2O}K_{S0}$ and $\Delta_{H_2O}G_{S0}$ for Fo90 and Fo100 are on the margins of being mutually consistent. Contrary to the prediction by Jacobsen et al. (2008, 2009), K_{S0} of Fo100 is slightly more reduced by H_2O compared to Fo90 and the two G'_0 's show similar reductions. However, $\Delta_{H_2O}K'_{S0}$ and $\Delta_{H_2O}G'_{S0}$ values are in excellent agreement within mutual uncertainties (Table 4). Therefore, the more pronounced effect observed by Mao et al. (2010) on hydrous Fo100 elastic properties arises by virtue of the higher water content, and not from a different effect of water in Fe-free and Fe-bearing samples as shown in Table 4. This also suggests that hydration is most likely to have a linear effect on the pressure derivatives of olivines.

3.4. Effect of hydration on sound wave velocities of Fo90 olivine and its geophysical implications

Using the new experimental data obtained in this study, we calculated the aggregate sound wave velocities of hydrous Fo90 olivine with 0.20 wt% H_2O as a function of pressure. Aggregate sound wave velocities of anhydrous Fo90 olivine are compared with those for hydrous olivine (Fig. 6). As the effect of temperature on the elasticity of hydrous olivine is currently unknown, all the calculations were performed at 300 K. In this context, Ye et al. (2009) showed that the thermal expansion coefficient of hydrous (0.89 wt% H_2O) end-member forsterite (Fo100) is marginally larger, $\sim 4.5(2.6)\%$, than that of Fo100. If this applies also for Fo90, the lower water content of our hydrous olivine (0.20 wt% H_2O) would have a negligible effect on its thermal expansion. Moreover, the effect of water on the thermal expansion of hydrous ($\sim 2.5 \text{ wt\% H}_2\text{O}$) wadsleyite and ringwoodite, i.e., the high-pressure polymorphs of olivine, seems to be negligible (Inoue et al., 2004). Therefore, we propose that H_2O is unlikely to have a significant effect on the thermal expansion of olivine.

The v_p and v_s of hydrous Fo90 follow similar trends to those of the elastic moduli (Fig. 6), with velocities being consistent with those of anhydrous Fo90 up to ~ 14 GPa. Mao et al. (2010) showed that v_p and v_s of the hydrous Fo100 cross and exceed those of the corresponding anhydrous phase at about 4 and 3 GPa, respectively, and rapidly diverge at higher pressure. The prominent rise of v_p and v_s with increasing pressure is due to the higher water content of the hydrous Fo100 sample employed by Mao et al. (2010) and not to a different effect of water in Fe-free and Fe-bearing samples, as shown in Table 4.

The 410-km global seismic discontinuity is widely accepted to be caused by the phase transition of olivine to its high pressure polymorph wadsleyite (Frost, 2008). Several works attempted to constrain the bulk olivine content in the upper mantle by comparing sound wave velocities of olivine and wadsleyite, calculated from either experimental or computational mineral physics data, with the observed seismic velocity contrasts across the discontinuity (e.g., Bass and Anderson, 1984; Dziewonski and Anderson, 1981; Núñez-Valdez et al., 2013; Wang et al., 2014, 2019). However, the calculated velocity contrasts across the discontinuity for a pyrolite composition ($\sim 60 \text{ vol\% olivine}$) are not consistent with global 1-D seismic models (e.g., Preliminary Earth Reference Model, PREM, or AK135; Dziewonski and Anderson, 1981; Kennett et al., 1995), pointing towards a bottom upper mantle that is

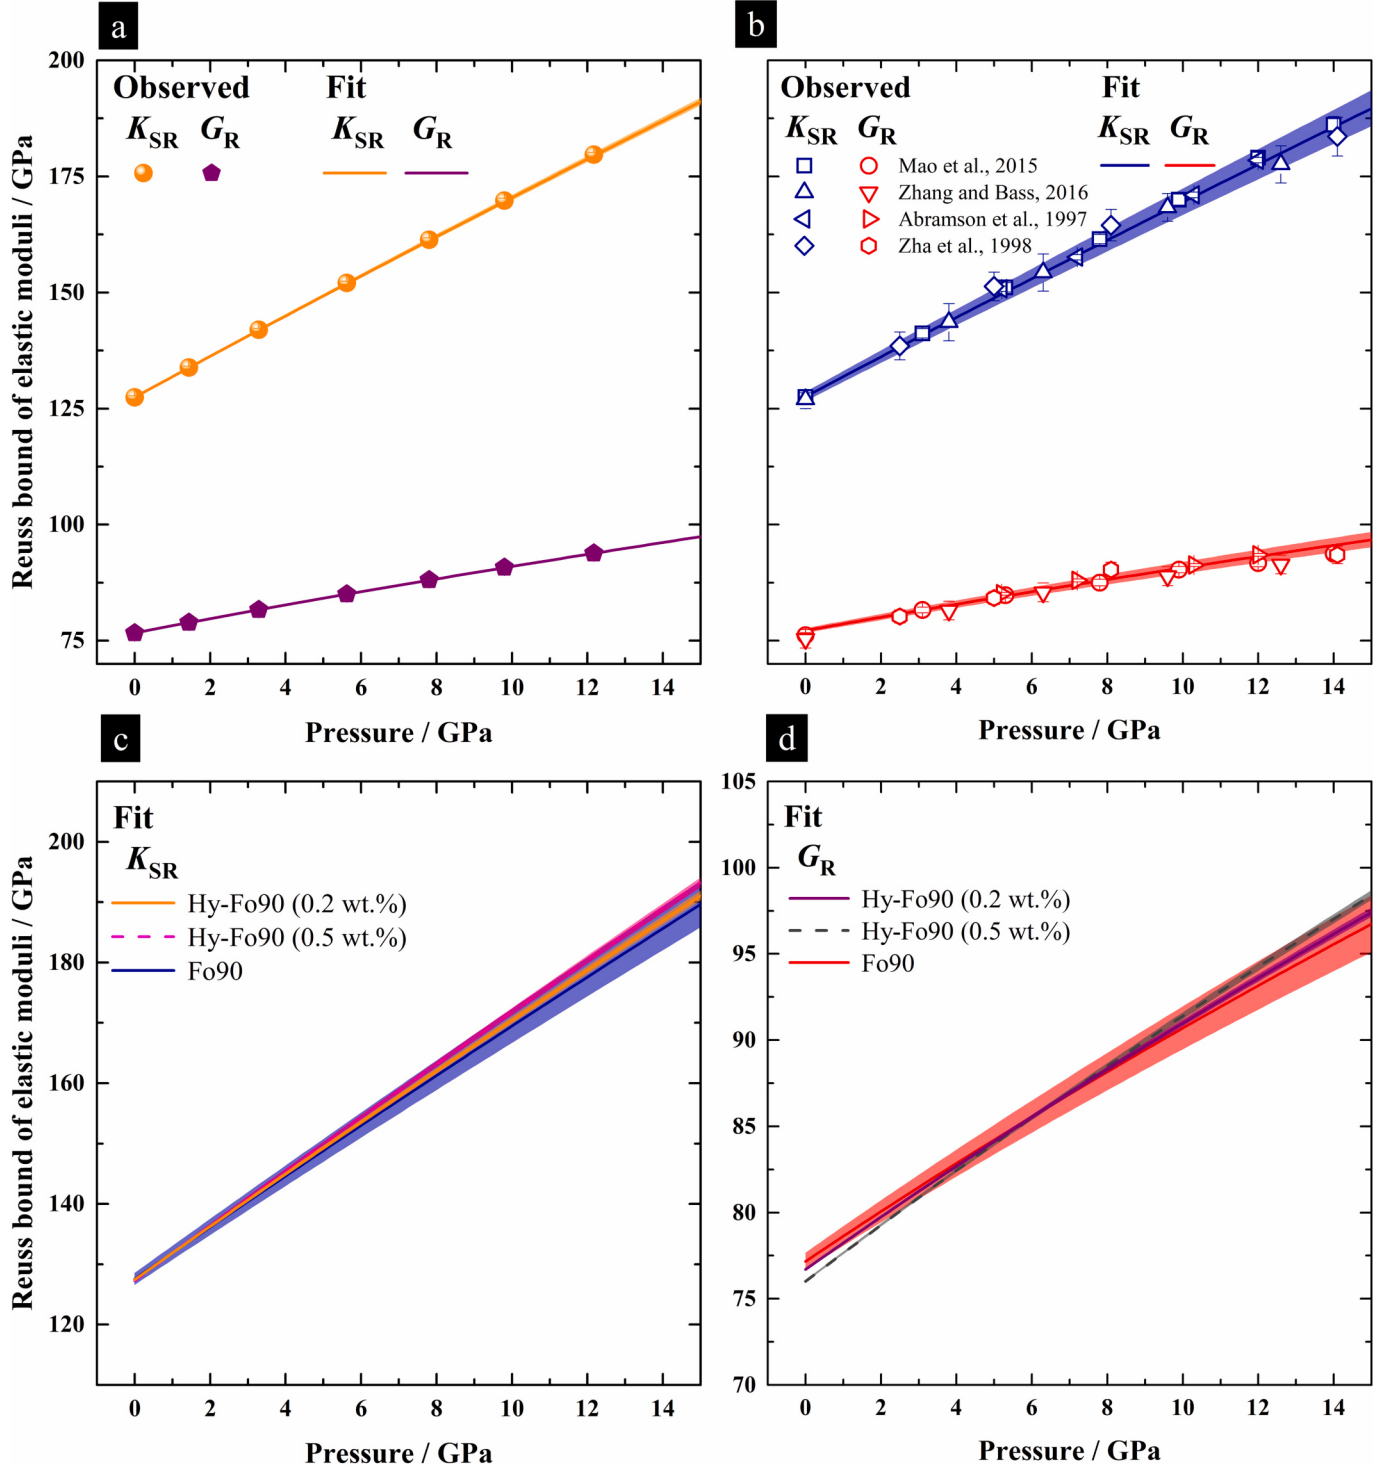


Fig. 5. (a) Variation as a function of pressure of the bulk (K) and shear (G) moduli of hydrous Fo90 calculated in the Reuss bound from the experimental high-pressure elasticity measurements of this study; the solid line and shaded area are the fit of the experimental data and the associated uncertainty, respectively. (b) Variation as a function of pressure of the bulk (K) and shear (G) moduli of anhydrous Fo90 calculated in the Reuss bound from previous experimental high-pressure elasticity measurements (Abramson et al., 1997; Mao et al., 2015; Zha et al., 1998; Zhang and Bass, 2016; Supplementary Table S2); the solid line and shaded area are the fit of the experimental data and the associated uncertainty, respectively. (c-d) Superimposition of fit curves for hydrous Fo90 and anhydrous Fo90 olivine; the dashed lines represent a linear extrapolation of the effect of incorporation of 0.5 wt% H₂O on the elastic properties of Fo90 olivine (see text and Table 4). Uncertainties are calculated by propagating the experimental errors on density and elastic moduli.

less olivine-rich than pyrolite. Considering the reduction of the sound wave velocities of wadsleyite due to the incorporation of water (Mao et al., 2008a, 2008b), it was proposed that water dissolved in olivine and wadsleyite may reconcile the pyrolite model with seismological

observations. Water is preferentially partitioned in wadsleyite ($D_{\text{wad/ol}} = 6$; Thio et al., 2016) and whether the presence of water can resolve seismological observations with pyrolitic mantle olivine contents will depend on both the expected amount of water in olivine and to what

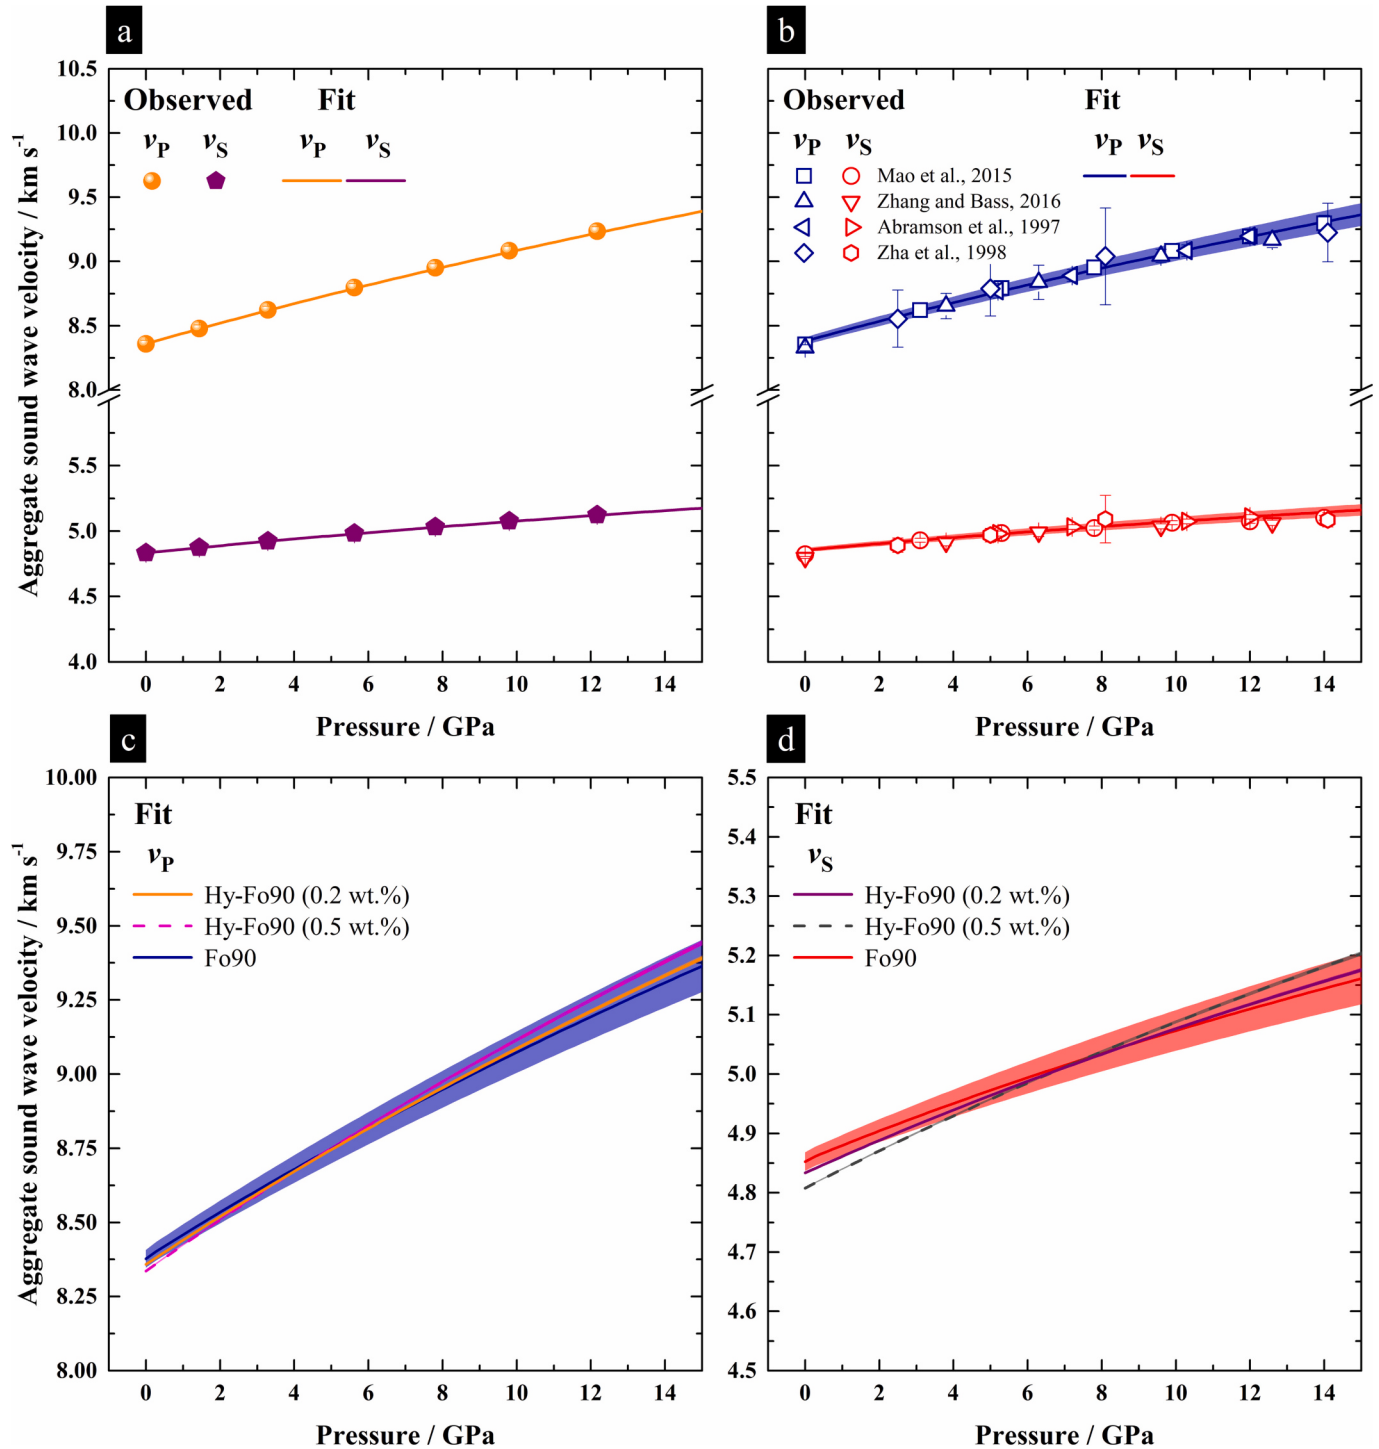


Fig. 6. (a) Variation as a function of pressure of the aggregate compressional and shear wave velocities of hydrous Fo90 calculated from the experimental high-pressure elasticity measurements of this study; the solid line and shaded area the fit of the experimental data and the associated uncertainty, respectively. (b) Variation as a function of pressure of the aggregate compressional and shear wave velocities of anhydrous Fo90 calculated from previous experimental high-pressure elasticity measurements (Abramson et al., 1997; Mao et al., 2015; Zha et al., 1998; Zhang and Bass, 2016; Supplementary Table S2); the solid line and shaded area the fit of the experimental data and the associated uncertainty, respectively. (c-d) Superimposition of fit curves for hydrous Fo90 and anhydrous Fo90 olivine. Uncertainties are calculated by propagating the experimental errors on density and elastic moduli.

extents it affects v_p and v_s of olivine. Available experimental data for hydrous olivine indicate storage capacities up to 0.9 wt% (Smyth et al., 2006), but the water content of olivine under relevant deep upper mantle conditions will be much lower, around 0.2–0.5 wt% H₂O (e.g., Férot and Bolfan-Casanova, 2012; Hirschmann et al., 2005; Mosenfelder, 2006). In this regard, our data are particularly significant and

indicate that the incorporation of ~0.20 wt% H₂O into Fo90 olivine crystal structure does not significantly affect its v_p and v_s at high pressure. To explore whether the presence of higher water contents in olivine would cause greater effects on its v_p and v_s , $\Delta_{H_2O}M$ values obtained for Fo90 were scaled to 0.5 wt% H₂O to determine the variations in K , K' , G and G' associated with the incorporation of such amount of

water and calculate the sound velocities of Fo90 hosting 0.5 wt% H₂O (Table 4, Figs. 5c–6c). Because hydration causes an increase in the unit-cell volume, the room pressure volume of Fo90 with 0.5 wt% H₂O was estimated using the expression $V_{0\text{ hydrous}} [\text{\AA}^3] = V_{0\text{ anhydrous}} [\text{\AA}^3] + 5.5 \times 10^{-5} [\text{\AA}^3] \times \text{H}_2\text{O} [\text{ppm}]$ from Smyth et al. (2006); $V_{0\text{ anhydrous}}$ was calculated using the same expression solved with the data of the hydrous olivine from this study (i.e., $V_0 = 291.65(2) \text{\AA}^3$ and ~ 2000 ppm). Then, the resulting volume of Fo90 with 0.5 wt% H₂O was converted into density. The calculated sound wave velocities for Fo90 with 0.5 wt% H₂O are reported in Fig. 6c and compared to those of hydrous Fo90 with 0.20 wt% H₂O and anhydrous Fo90. The incorporation of 0.5 wt% H₂O into Fo90 olivine slightly reduces its elastic moduli (mostly G) and sound wave velocities at ambient pressure (Table 4, Figs. 5c–6c). Nonetheless, v_p and v_s of the hydrous phase become indistinguishable within uncertainties with those of the anhydrous phase at pressures exceeding ~ 2 and ~ 5 GPa, owing to the larger K'_{S0} and G'_0 . This advises caution when speculating on the water content in the deep upper mantle based on its effect on olivine elastic properties and seismic wave velocities. Furthermore, our data also suggest that H₂O incorporation in olivine may not reconcile seismological observations at the 410-km discontinuity with a pyrolitic mantle, although we are aware that direct determinations of sound wave velocities of hydrous olivine and hydrous wadsleyite at combined HP–HT (e.g., Buchen et al., 2018) are needed to refine these findings.

The discrepancy between the observed and calculated wave velocities for a pyrolite composition may also arise from strong variations of olivine content and upper mantle lithologies near the 410-km seismic discontinuity, for which corroborating evidence has been found by Zhang and Bass (2016). Indeed, olivine contents inferred from regional seismic models of the Pacific region are extremely variable and increase from approximately 20–40% in the central Pacific to 60–90% in the western U.S. and eastern Pacific regions. Given the indistinguishable seismic behaviour of hydrous and anhydrous Fo90 olivine at high pressure, we argue that this high degree of heterogeneity does not stem from the potentially different responses of dry and wet regions of the deep upper mantle, but rather may arise from variations in olivine content.

4. Concluding remarks

The sound velocities and single-crystal elastic coefficients of Fo90 olivine with 0.20 wt% H₂O were measured up to ~ 12 GPa at room temperature by simultaneous single-crystal X-ray diffraction and Brillouin scattering experiments. Compared to the anhydrous phase, K and G of hydrous Fo90 at ambient conditions are virtually identical, while their pressure derivatives are slightly larger, although consistent within mutual uncertainties. For this reason, the elastic behaviour of hydrous and anhydrous Fo90 olivine is indistinguishable within uncertainties up to pressures corresponding to the base of the upper mantle. Using our new accurate data, we investigated the effect of hydration on aggregate sound velocities of Fo90. At ambient pressure, the compressional and shear wave velocities of hydrous Fo90 with 0.2 and 0.5 wt% H₂O are identical to, or slightly slower than, those of the anhydrous phase. In both cases however, v_p and v_s of the hydrous and anhydrous phases are indistinguishable within uncertainties at deep upper mantle conditions. Therefore, if amounts of water were to be incorporated into Fo90 olivine crystal structure, its elastic and seismic behaviour at high pressure may remain unchanged. Based on our findings, we suggest that water in olivine is not seismically detectable, at least for contents up to 0.2–0.5 wt%, i.e., the amount of water expected in olivine at deep upper mantle conditions. We therefore advise caution about speculations of the water content in the deep upper mantle based on its effect on olivine elastic properties and sound wave velocities. In addition, our data also suggest that the hydration of olivine is unlikely to be a key factor in reconciling seismic velocity and density contrasts across the 410-km discontinuity with a pyrolitic mantle.

CRedit authorship contribution statement

Luca Faccincani: Conceptualization, Methodology, Formal analysis, Investigation, Data curation, Writing – original draft, Writing – review & editing. **Giacomo Criniti:** Methodology, Formal analysis, Investigation, Data curation, Writing – review & editing. **Alexander Kurnosov:** Methodology, Investigation, Writing – review & editing. **Tiziana Boffa Ballaran:** Methodology, Investigation, Writing – review & editing, Supervision. **Anthony C. Withers:** Investigation, Writing – review & editing. **Maurizio Mazzucchelli:** Writing – review & editing, Supervision. **Fabrizio Nestola:** Writing – review & editing, Supervision. **Massimo Coltorti:** Conceptualization, Writing – review & editing, Supervision.

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Data availability

All data derived from this research are presented in the enclosed tables, figures, and supplementary data.

Acknowledgements

The authors would like to thank R. Njål for his help in double-side polishing the two single crystals to platelets and D. Wiesner for her help in the operation of the FIB device. L.F. acknowledges Istituto Nazionale di Geofisica e Vulcanologia (INGV) for funding his Ph.D. project (XXXV cycle) with thematic ‘Links between rheology, mineralogy and composition of the Earth’s mantle’ and the University of Ferrara for the 2021 IUSS international mobility program. This research was also supported by the Italian National Research Program (PRIN Grant 20178LPCPW-‘Micro to Macro – How to unravel the nature of the Large Magmatic Events’ to M.C.).

Appendix A. Supplementary data

Supplementary data to this article can be found online at <https://doi.org/10.1016/j.pepi.2023.107011>.

References

- Abramson, E.H., Brown, J.M., Slutsky, L.J., Zaug, J., 1997. The elastic constants of San Carlos olivine to 17 GPa. *J. Geophys. Res. Solid Earth* 102, 12253–12263. <https://doi.org/10.1029/97JB00682>.
- Angel, R.J., 2000. Equations of state. *Rev. Mineral. Geochem.* 41, 35–59. <https://doi.org/10.2138/rmg.2000.41.2>.
- Angel, R.J., Finger, L.W., 2011. SINGLE : a program to control single-crystal diffractometers. *J. Appl. Crystallogr.* 44, 247–251. <https://doi.org/10.1107/S0021889810042305>.
- Angel, R.J., Alvaro, M., Gonzalez-Platas, J., 2014. EosFit7c and a Fortran module (library) for equation of state calculations. *Zeitschrift für Krist. - Cryst. Mater.* 229, 405–419. <https://doi.org/10.1515/zkri-2013-1711>.
- Angel, R.J., Alvaro, M., Nestola, F., 2018. 40 years of mineral elasticity: a critical review and a new parameterisation of equations of state for mantle olivines and diamond inclusions. *Phys. Chem. Miner.* 45, 95–113. <https://doi.org/10.1007/s00269-017-0900-7>.
- Bali, E., Bolfan-Casanova, N., Koga, K.T., 2008. Pressure and temperature dependence of H solubility in forsterite: an implication to water activity in the Earth interior. *Earth Planet. Sci. Lett.* 268, 354–363. <https://doi.org/10.1016/j.epsl.2008.01.035>.
- Bass, J.D., Anderson, D.L., 1984. Composition of the upper mantle: geophysical tests of two petrological models. *Geophys. Res. Lett.* 11, 229–232. <https://doi.org/10.1029/GL011i003p00229>.
- Bell, D.R., Rossman, G.R., 1992. Water in Earth’s mantle: the role of nominally anhydrous minerals. *Science* 255, 1391–1397. <https://doi.org/10.1126/science.255.5050.1391>.
- Beran, A., Libowitzky, E., 2006. Water in natural mantle minerals II: Olivine, garnet and accessory minerals. In: *Reviews in Mineralogy and Geochemistry* 62: Water in

- Nominally Anhydrous Minerals, pp. 169–192. <https://doi.org/10.2138/rmg.2006.62.8>.
- Boehler, R., De Hantsetters, K., 2004. New anvil designs in diamond-cells. *High Pressure Res.* 24, 391–396. <https://doi.org/10.1080/08957950412331323924>.
- Bonadiman, C., Hao, Y., Coltorti, M., Dallai, L., Faccini, B., Huang, Y.X., 2009. Water contents of pyroxenes in intraplate lithospheric mantle. *Eur. J. Mineral.* 21, 637–647. <https://doi.org/10.1127/0935-1221/2009/0021-1935>.
- Brodholt, J.P., Refson, K., 2000. An ab initio study of hydrogen in forsterite and a possible mechanism for hydrolytic weakening. *J. Geophys. Res. Solid Earth* 105, 18977–18982. <https://doi.org/10.1029/2000JB900057>.
- Buchen, J., 2018. The Elastic Properties of Wadsleyite and Stishovite at High Pressures: Tracing Deep Earth Material Cycles. University of Bayreuth. <https://doi.org/10.15495/EPUB-UBT-00004410>.
- Buchen, J., Marquardt, H., Speziale, S., Kawazoe, T., Boffa Ballaran, T., Kurnosov, A., 2018. High-pressure single-crystal elasticity of wadsleyite and the seismic signature of water in the shallow transition zone. *Earth Planet. Sci. Lett.* 498, 77–87. <https://doi.org/10.1016/j.epsl.2018.06.027>.
- Chang, Y.-Y., Hsieh, W.-P., Tan, E., Chen, J., 2017. Hydration-reduced lattice thermal conductivity of olivine in Earth's upper mantle. *Proc. Natl. Acad. Sci.* 114, 4078–4081. <https://doi.org/10.1073/pnas.1616216114>.
- Costa, F., Chakraborty, S., 2008. The effect of water on Si and O diffusion rates in olivine and implications for transport properties and processes in the upper mantle. *Phys. Earth Planet. Inter.* 166, 11–29. <https://doi.org/10.1016/j.pepi.2007.10.006>.
- Criniti, G., Kurnosov, A., Boffa Ballaran, T., Frost, D.J., 2021. Single-crystal elasticity of MgSiO₃ Bridgmanite to mid-lower mantle pressure. *J. Geophys. Res. Solid Earth* 126. <https://doi.org/10.1029/2020JB020967>.
- Demouchy, S., Mackwell, S., 2006. Mechanisms of hydrogen incorporation and diffusion in iron-bearing olivine. *Phys. Chem. Miner.* 33, 347–355. <https://doi.org/10.1007/s00269-006-0081-2>.
- Demouchy, S., Jacobsen, S.D., Gaillard, F., Stern, C.R., 2006. Rapid magma ascent recorded by water diffusion profiles in mantle olivine. *Geology* 34, 429. <https://doi.org/10.1130/G22386.1>.
- Downs, R.T., Zha, C.-S., Duffy, T.S., Finger, L.W., 1996. The equation of state of forsterite to 17.2 GPa and effects of pressure media. *Am. Mineral.* 81, 51–55. <https://doi.org/10.2138/am-1996-1-207>.
- Dziewonski, A.M., Anderson, D.L., 1981. Preliminary reference Earth model. *Phys. Earth Planet. Inter.* 25, 297–356. [https://doi.org/10.1016/0031-9201\(81\)90046-7](https://doi.org/10.1016/0031-9201(81)90046-7).
- Faccincani, L., Faccini, B., Casetta, F., Mazzucchelli, M., Nestola, F., Coltorti, M., 2021. EoS of mantle minerals coupled with composition and thermal state of the lithosphere: inferring the density structure of peridotitic systems. *Lithos* 404–405, 106483. <https://doi.org/10.1016/j.lithos.2021.106483>.
- Fei, H., Katsura, T., 2020. Pressure dependence of proton incorporation and water solubility in olivine. *J. Geophys. Res. Solid Earth* 125, 1–13. <https://doi.org/10.1029/2019JB018813>.
- Férot, A., Bolfan-Casanova, N., 2012. Water storage capacity in olivine and pyroxene to 14GPa: implications for the water content of the Earth's upper mantle and nature of seismic discontinuities. *Earth Planet. Sci. Lett.* 349–350, 218–230. <https://doi.org/10.1016/j.epsl.2012.06.022>.
- Frost, D.J., 2008. The upper mantle and transition zone. *Elements* 4, 171–176. <https://doi.org/10.2113/GSELEMENTS.4.3.171>.
- Hirschmann, M.M., Aubaud, C., Withers, A.C., 2005. Storage capacity of H₂O in nominally anhydrous minerals in the upper mantle. *Earth Planet. Sci. Lett.* 236, 167–181. <https://doi.org/10.1016/j.epsl.2005.04.022>.
- Hushur, A., Manghnani, M.H., Smyth, J.R., Nestola, F., Frost, D.J., 2009. Crystal chemistry of hydrous forsterite and its vibrational properties up to 41 GPa. *Am. Mineral.* 94, 751–760. <https://doi.org/10.2138/am.2009.2990>.
- Inoue, T., 1994. Effect of water on melting phase relations and melt composition in the system Mg₂SiO₄-MgSiO₃-H₂O up to 15 GPa. *Phys. Earth Planet. Inter.* 85, 237–263. [https://doi.org/10.1016/0031-9201\(94\)90116-3](https://doi.org/10.1016/0031-9201(94)90116-3).
- Inoue, T., Tanimoto, Y., Irifune, T., Suzuki, T., Fukui, H., Ohtaka, O., 2004. Thermal expansion of wadsleyite, ringwoodite, hydrous wadsleyite and hydrous ringwoodite. *Phys. Earth Planet. Inter.* 143–144, 279–290. <https://doi.org/10.1016/j.pepi.2003.07.021>.
- Jacobsen, S.D., Jiang, F., Mao, Z., Duffy, T.S., Smyth, J.R., Holl, C.M., Frost, D.J., 2008. Effects of hydration on the elastic properties of olivine. *Geophys. Res. Lett.* 35, L14303. <https://doi.org/10.1029/2008GL034398>.
- Jacobsen, S.D., Jiang, F., Mao, Z., Duffy, T.S., Smyth, J.R., Holl, C.M., Frost, D.J., 2009. Correction to “Effects of hydration on the elastic properties of olivine.”. *Geophys. Res. Lett.* 36, L12302. <https://doi.org/10.1029/2009GL038660>.
- Jung, H., Karato, S.-I., 2001. Effects of water on dynamically recrystallized grain-size of olivine. *J. Struct. Geol.* 23, 1337–1344. [https://doi.org/10.1016/S0191-8141\(01\)00005-0](https://doi.org/10.1016/S0191-8141(01)00005-0).
- Kantor, I., Prakapenka, V., Kantor, A., Dera, P., Kurnosov, A., Sinogeikin, S., Dubrovinskaya, N., Dubrovinsky, L., 2012. BX90: a new diamond anvil cell design for X-ray diffraction and optical measurements. *Rev. Sci. Instrum.* 83, 125102. <https://doi.org/10.1063/1.4768541>.
- Kennett, B.L.N., Engdahl, E.R., Buland, R., 1995. Constraints on seismic velocities in the Earth from traveltimes. *Geophys. J. Int.* 122, 108–124. <https://doi.org/10.1111/j.1365-246X.1995.tb03540.x>.
- King, H.E., Finger, L.W., 1979. Diffracted beam crystal centering and its application to high-pressure crystallography. *J. Appl. Crystallogr.* 12, 374–378. <https://doi.org/10.1107/S0021889879012723>.
- Kurnosov, A., Kantor, I., Boffa-Ballaran, T., Lindhardt, S., Dubrovinsky, L., Kuznetsov, A., Zehnder, B.H., 2008. A novel gas-loading system for mechanically closing of various types of diamond anvil cells. *Rev. Sci. Instrum.* 79, 045110. <https://doi.org/10.1063/1.2902506>.
- Kurnosov, A., Marquardt, H., Frost, D.J., Ballaran, T.B., Ziberna, L., 2017. Evidence for a Fe³⁺-rich pyrolytic lower mantle from (Al,Fe)-bearing bridgmanite elasticity data. *Nature* 543, 543–546. <https://doi.org/10.1038/nature21390>.
- Mao, Z., Jacobsen, S.D., Jiang, F., Smyth, J.R., Holl, C.M., Duffy, T.S., 2008a. Elasticity of hydrous wadsleyite to 12 GPa: implications for Earth's transition zone. *Geophys. Res. Lett.* 35, L21305. <https://doi.org/10.1029/2008GL035618>.
- Mao, Z., Jacobsen, S.D., Jiang, F.M., Smyth, J.R., Holl, C.M., Frost, D.J., Duffy, T.S., 2008b. Single-crystal elasticity of wadsleyites, β -Mg₂SiO₄, containing 0.37–1.66 wt. % H₂O. *Earth Planet. Sci. Lett.* 268, 540–549. <https://doi.org/10.1016/j.epsl.2008.01.023>.
- Mao, Z., Jacobsen, S.D., Jiang, F., Smyth, J.R., Holl, C.M., Frost, D.J., Duffy, T.S., 2010. Velocity crossover between hydrous and anhydrous forsterite at high pressures. *Earth Planet. Sci. Lett.* 293, 250–258. <https://doi.org/10.1016/j.epsl.2010.02.025>.
- Mao, Z., Fan, D., Lin, J.-F., Yang, J., Tkachev, S.N., Zhuravlev, K., Prakapenka, V.B., 2015. Elasticity of single-crystal olivine at high pressures and temperatures. *Earth Planet. Sci. Lett.* 426, 204–215. <https://doi.org/10.1016/j.epsl.2015.06.045>.
- Matveev, S., O'Neill, H.S.C., Ballhaus, C., Taylor, W.R., Green, D.H., 2001. Effect of silica activity on OH- IR spectra of olivine: implications for low-aSiO₂ mantle metasomatism. *J. Petrol.* 42, 721–729. <https://doi.org/10.1093/petrology/42.4.721>.
- Mosenfelder, J.L., 2006. Hydrogen incorporation in olivine from 2–12 GPa. *Am. Mineral.* 91, 285–294. <https://doi.org/10.2138/am.2006.1943>.
- Nestola, F., Nimis, P., Ziberna, L., Longo, M., Marzoli, A., Harris, J.W., Manghnani, M.H., Fedortchouk, Y., 2011. First crystal-structure determination of olivine in diamond: composition and implications for provenance in the Earth's mantle. *Earth Planet. Sci. Lett.* 305, 249–255. <https://doi.org/10.1016/j.epsl.2011.03.007>.
- Novella, D., Bolfan-Casanova, N., Nestola, F., Harris, J.W., 2015. H₂O in olivine and garnet inclusions still trapped in diamonds from the Siberian craton: implications for the water content of cratonic lithosphere peridotites. *Lithos* 230, 180–183. <https://doi.org/10.1016/j.lithos.2015.05.013>.
- Núñez-Valdez, M., Wu, Z., Yu, Y.G., Wentzcovitch, R.M., 2013. Thermal elasticity of (Fe_xMg_{1-x})₂SiO₄ olivine and wadsleyite. *Geophys. Res. Lett.* 40, 290–294. <https://doi.org/10.1002/grl.50131>.
- Nye, J.F., 1985. *Physical Properties of Crystals: Their Representation by Tensors and Matrices*. Oxford university press.
- Pamato, M.G., Nestola, F., Novella, D., Smyth, J.R., Pasqual, D., Gatta, G.D., Alvaro, M., Secco, L., 2019. The high-pressure structural evolution of olivine along the Forsterite–Fayalite join. *Minerals* 9, 790. <https://doi.org/10.3390/min9120790>.
- Peslier, A.H., 2010. A review of water contents of nominally anhydrous natural minerals in the mantles of Earth, Mars and the Moon. *J. Volcanol. Geotherm. Res.* 197, 239–258. <https://doi.org/10.1016/j.jvolgeores.2009.10.006>.
- Peslier, A.H., Woodland, A.B., Wolff, J.A., 2008. Fast kimberlite ascent rates estimated from hydrogen diffusion profiles in xenolithic mantle olivines from southern Africa. *Geochim. Cosmochim. Acta* 72, 2711–2722. <https://doi.org/10.1016/j.gca.2008.03.019>.
- Peslier, A.H., Woodland, A.B., Bell, D.R., Lazarov, M., 2010. Olivine water contents in the continental lithosphere and the longevity of cratons. *Nature* 467, 78–81. <https://doi.org/10.1038/nature09317>.
- Ralph, R.L., Finger, L.W., 1982. A computer program for refinement of crystal orientation matrix and lattice constants from diffractometer data with lattice symmetry constraints. *J. Appl. Crystallogr.* 15, 537–539. <https://doi.org/10.1107/S0021889882012539>.
- Regenauer-Lieb, K., 2006. Water and geodynamics. *Rev. Mineral. Geochem.* 62, 451–473. <https://doi.org/10.2138/rmg.2006.62.19>.
- Ringwood, A.E., 1975. *Composition and Petrology of the Earth's Mantle*. Mac Graw-Hill Book Company.
- Sandercock, J.R., 1982. Trends in Brillouin scattering: Studies of opaque materials, supported films, and central modes. In: Cardona, M., Güntherodt, G. (Eds.), *Light Scattering in Solids III: Recent Results*. Springer, Berlin Heidelberg, Berlin, Heidelberg, pp. 173–206. https://doi.org/10.1007/3540115137_6.
- Schulze, K., Buchen, J., Marquardt, K., Marquardt, H., 2017. Multi-sample loading technique for comparative physical property measurements in the diamond-anvil cell. *High Pressure Res.* 37, 159–169. <https://doi.org/10.1080/08957959.2017.1299719>.
- Shen, G., Wang, Y., Dewaele, A., Wu, C., Fratanuono, D.E., Eggert, J., Klotz, S., Dziubek, K.F., Loubeyre, P., Fat'yanov, O.V., Asimow, P.D., Mashimo, T., Wentzcovitch, R.M.M., 2020. Toward an international practical pressure scale: a proposal for an IPPS ruby gauge (IPPS-Ruby2020). *High Pressure Res.* 40, 299–314. <https://doi.org/10.1080/08957959.2020.1791107>.
- Smyth, J.R., Frost, D.J., Nestola, F., Holl, C.M., Bromiley, G., 2006. Olivine hydration in the deep upper mantle: effects of temperature and silica activity. *Geophys. Res. Lett.* 33, L15301. <https://doi.org/10.1029/2006GL026194>.
- Speziale, S., Marquardt, H., Duffy, T.S., 2014. Brillouin scattering and its application in geosciences. *Rev. Mineral. Geochem.* 543–603. <https://doi.org/10.2138/rmg.2014.78.14>.
- Stixrude, L., Lithgow-Bertelloni, C., 2005. Thermodynamics of mantle minerals - I. Physical properties. *Geophys. J. Int.* 162, 610–632. <https://doi.org/10.1111/j.1365-246X.2005.02642.x>.
- Thio, V., Cobden, L., Trampert, J., 2016. Seismic signature of a hydrous mantle transition zone. *Phys. Earth Planet. Inter.* 250, 46–63. <https://doi.org/10.1016/j.pepi.2015.11.005>.
- Trots, D.M., Kurnosov, A., Vasylechko, L., Berkowski, M., Boffa Ballaran, T., Frost, D.J., 2011. Elasticity and equation of state of Li₂B₄O₇. *Phys. Chem. Miner.* 38, 561–567. <https://doi.org/10.1007/s00269-011-0428-1>.
- Trots, D.M., Kurnosov, A., Ballaran, T.B., Tkachev, S., Zhuravlev, K., Prakapenka, V., Berkowski, M., Frost, D.J., 2013. The Sm:YAG primary fluorescence pressure scale.

- J. Geophys. Res. Solid Earth 118, 5805–5813. <https://doi.org/10.1002/2013JB010519>.
- Umemoto, K., Wentzcovitch, R.M., Hirschmann, M.M., Kohlstedt, D.L., Withers, A.C., 2011. A first-principles investigation of hydrous defects and IR frequencies in forsterite: the case for Si vacancies. *Am. Mineral.* 96, 1475–1479. <https://doi.org/10.2138/am.2011.3720>.
- Wang, J., Bass, J.D., Kastura, T., 2014. Elastic properties of iron-bearing wadsleyite to 17.7GPa: implications for mantle mineral models. *Phys. Earth Planet. Inter.* 228, 92–96. <https://doi.org/10.1016/j.pepi.2014.01.015>.
- Wang, W., Walter, M.J., Peng, Y., Redfern, S., Wu, Z., 2019. Constraining olivine abundance and water content of the mantle at the 410-km discontinuity from the elasticity of olivine and wadsleyite. *Earth Planet. Sci. Lett.* 519, 1–11. <https://doi.org/10.1016/j.epsl.2019.04.018>.
- Whitfield, C.H., Brody, E.M., Bassett, W.A., 1976. Elastic moduli of NaCl by Brillouin scattering at high pressure in a diamond anvil cell. *Rev. Sci. Instrum.* 47, 942–947. <https://doi.org/10.1063/1.1134778>.
- Withers, A.C., Hirschmann, M.M., 2008. Influence of temperature, composition, silica activity and oxygen fugacity on the H₂O storage capacity of olivine at 8 GPa. *Contrib. Mineral. Petrol.* 156, 595–605. <https://doi.org/10.1007/s00410-008-0303-3>.
- Withers, A.C., Hirschmann, M.M., Tenner, T.J., 2011. The effect of Fe on olivine H₂O storage capacity: consequences for H₂O in the martian mantle. *Am. Mineral.* 96, 1039–1053. <https://doi.org/10.2138/am.2011.3669>.
- Withers, A.C., Bureau, H., Raepsaet, C., Hirschmann, M.M., 2012. Calibration of infrared spectroscopy by elastic recoil detection analysis of H in synthetic olivine. *Chem. Geol.* 334, 92–98. <https://doi.org/10.1016/j.chemgeo.2012.10.002>.
- Xia, Q.-K., Hao, Y., Li, P., Deloule, E., Coltorti, M., Dallai, L., Yang, X., Feng, M., 2010. Low water content of the Cenozoic lithospheric mantle beneath the eastern part of the North China Craton. *J. Geophys. Res.* 115, B07207. <https://doi.org/10.1029/2009JB006694>.
- Xu, J., Fan, D., Zhang, D., Li, B., Zhou, W., Dera, P.K., 2020. Investigation of the crystal structure of a low water content hydrous olivine to 29.9 GPa: a high-pressure single-crystal X-ray diffraction study. *Am. Mineral.* 105, 1857–1865. <https://doi.org/10.2138/am-2020-7444>.
- Xue, X., Kanzaki, M., Turner, D., Loroch, D., 2017. Hydrogen incorporation mechanisms in forsterite: new insights from 1 H and 29 Si NMR spectroscopy and first-principles calculation. *Am. Mineral.* 102, 519–536. <https://doi.org/10.2138/am-2017-5878>.
- Ye, Y., Schwering, R.A., Smyth, J.R., 2009. Effects of hydration on thermal expansion of forsterite, wadsleyite, and ringwoodite at ambient pressure. *Am. Mineral.* 94, 899–904. <https://doi.org/10.2138/am.2009.3122>.
- Zha, C., Duffy, T.S., Downs, R.T., Mao, H., Hemley, R.J., 1998. Brillouin scattering and X-ray diffraction of San Carlos olivine: direct pressure determination to 32 GPa. *Earth Planet. Sci. Lett.* 159, 25–33. [https://doi.org/10.1016/S0012-821X\(98\)00063-6](https://doi.org/10.1016/S0012-821X(98)00063-6).
- Zhang, J.S., Bass, J.D., 2016. Sound velocities of olivine at high pressures and temperatures and the composition of Earth's upper mantle. *Geophys. Res. Lett.* 43, 9611–9618. <https://doi.org/10.1002/2016GL069949>.
- Zha, C., Duffy, T.S., Downs, R.T., Mao, H., Hemley, R.J., 1996. Sound velocity and elasticity of single-crystal forsterite to 16 GPa. *J. Geophys. Res. Solid Earth* 101, 17535–17545.